



BSI Standards Publication

<https://www.china-gauges.com/>

Aluminium and aluminium alloys — Coil coated sheet and strip for general applications — Specifications

National foreword

This British Standard is the UK implementation of EN 1396:2023. It supersedes BS EN 1396:2015, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee NFE/35, Light metals and their alloys.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

© The British Standards Institution 2023
Published by BSI Standards Limited 2023

ISBN 978 0 539 19725 9

ICS 77.150.10

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 30 June 2023.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

EUROPEAN STANDARD

EN 1396

NORME EUROPÉENNE

EUROPÄISCHE NORM

June 2023

ICS 77.150.10

Supersedes EN 1396:2015

English Version

Aluminium and aluminium alloy coil coated sheet and strip for general applications - Specifications

Aluminium et alliages d'aluminium - Tôles et bandes revêtues en continu pour applications générales - Spécifications

Aluminium und Aluminiumlegierungen - Bandbeschichtete Bleche und Bänder für allgemeine Anwendungen - Spezifikationen

This European Standard was approved by CEN on 7 May 2023.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents

	Page
European foreword.....	4
Introduction	5
1 Scope.....	6
2 Normative references.....	6
3 Terms and definitions	6
4 Technical conditions for inspection and delivery.....	8
4.1 Ordering information	8
4.2 Requirements.....	10
4.2.1 Production and manufacturing processes	10
4.2.2 Quality control	10
4.2.3 Freedom from defects.....	11
4.2.4 Chemical composition	11
4.2.5 Mechanical properties.....	11
4.2.6 Tolerances on shape and dimensions.....	11
4.2.7 Coating properties	11
4.3 Test procedures.....	11
4.3.1 Chemical composition	11
4.3.2 Tensile test	11
4.3.3 Coating tests	12
4.3.4 Retests.....	12
5 Mechanical properties.....	12
6 Organic coating properties.....	15
6.1 Tolerances on thickness	15
6.2 Tolerances on gloss	16
6.3 Tolerances on colour	17
7 Inspection documents	17
8 Marking.....	17
9 Packing.....	18
10 Arbitration tests	18
Annex A (normative) Rules for rounding	19
Annex B (informative) Examples of coating systems	20
Annex C (informative) Guidelines for organic coatings.....	22
C.1 General.....	22
C.2 Colour	22
C.3 Flexibility	22
C.4 Adhesion.....	23
C.5 Pencil hardness.....	24
C.6 Durability of the organic coating.....	24
C.6.1 General.....	24

C.6.2	Corrosion resistance (outdoor exposure)	26
C.6.3	UV resistance	27
C.6.4	Humidity and water immersion resistance (accelerated tests)	29
C.6.5	Acetic acid salt spray fog resistance (accelerated corrosion test)	29
C.6.6	Filiform corrosion test, FFC (accelerated corrosion test)	30
Annex D (informative)	Guidelines for storage and subsequent processing	31
D.1	Storage	31
D.2	General instructions for processing	31
D.3	Forming	31
D.4	Cutting	31
D.5	Joining	32
D.6	Cleaning	32
D.7	Temporary protective films	32
	Bibliography	33

European foreword

This document (EN 1396:2023) has been prepared by Technical Committee CEN/TC 132 “Aluminium and aluminium alloys”, the secretariat of which is held by AFNOR.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by December 2023, and conflicting national standards shall be withdrawn at the latest by December 2023.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 1396:2015.

Any feedback and questions on this document should be directed to the users' national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

Introduction

Organic coated aluminium and aluminium alloy strip and sheet products can be used to advantage in cases where corrosion resistance and decorative appearance are of primary importance. They have applications throughout the flat products processing industry e.g. in the building, automotive, caravans, appliances, fabricating and packaging industries.

Organic coated aluminium and aluminium alloy flat products can be delivered in numerous types and grades, depending on the base material used (various grades of aluminium), on the coating material and types of coating and on the requirements for the surface appearance and the formability.

The properties of the products can vary within greater or smaller limits depending on the choice and combination of properties required. It is therefore not practicable to specify in detail minimum requirements for all properties for all types of products.

As a general rule, material specifications are agreed between manufacturer and user/purchaser using, when appropriate, the guidelines from Annex C.

Guidelines for proper storage and subsequent processing of organic coated aluminium and aluminium alloy flat products are given in Annex D.

1 Scope

This document specifies the particular requirements for wrought aluminium and wrought aluminium alloys in the form of coil coated sheet and strip for general applications. This product is generally supplied in thicknesses up to 3,0 mm.

It is applicable to cold-rolled aluminium and aluminium alloy strip coated by the coil coating process both with liquid as well as with powder paints, either in the final width or slit afterwards, and to sheet obtained from such strip.

It does not apply to coil coated sheet and strip used for special applications such as cans, closures and lids which are dealt with in separate EN 541.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 485-1, *Aluminium and aluminium alloys - Sheet, strip and plate - Part 1: Technical conditions for inspection and delivery*

EN 485-4, *Aluminium and aluminium alloys - Sheet, strip and plate - Part 4: Tolerances on shape and dimensions for cold-rolled products*

EN 515, *Aluminium and aluminium alloys - Wrought products - Temper designations*

EN 573-3, *Aluminium and aluminium alloys - Chemical composition and form of wrought products - Part 3: Chemical composition and form of products*

EN 12258-1, *Aluminium and aluminium alloys - Terms and definitions - Part 1: General terms*

EN 13523-1, *Coil coated metals - Test methods - Part 1: Film thickness*

EN 13523-2, *Coil coated metals - Test methods - Part 2: Gloss*

EN 13523-3, *Coil coated metals - Test methods - Part 3: Colour difference and metamerism - Instrumental comparison*

EN 13523-22, *Coil coated metals - Test methods - Part 22: Colour difference - Visual comparison*

EN ISO 6892-1, *Metallic materials - Tensile testing - Part 1: Method of test at room temperature (ISO 6892-1)*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in EN 12258-1 and the following apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

aluminium

unalloyed aluminium or aluminium alloy

Note 1 to entry: In the USA the term "Aluminum" is used.

3.2

aluminium alloy

aluminium which contains alloying elements, where aluminium predominates by mass over each of the other elements and where the aluminium content is not greater than 99,00 %

3.3

metal substrate

base material from cold rolled aluminium or aluminium alloy strip

3.4

coating material

material comprising organic polymers e.g. synthetic resins or plastics, to which pigments, additives and sol-vents (if required) have generally been added, suitable for coil coating

Note 1 to entry: These can be paints (liquid or powder) or plastic films.

3.5

coil coating

method in which a coating material is applied in a continuous process on a cold rolled metal strip

Note 1 to entry: This process includes cleaning and chemical pre-treatment of the surface and either:

- one-side or two-side, single or multiple application of liquid or powder coating materials which are subsequently cured; or
- laminating with plastic films.

3.6

organic coating

paint or lacquer film on a coated product produced from wet paint or from powder coating, or the laminated organic film

3.7

top side

side of the strip with the highest decorative demand and which, in normal production, is uppermost

Note 1 to entry: For strip supplied in coil form, the top side is normally the outside of the coil. For sheet supplied in stacks or bundles the top side is normally uppermost.

3.8

reverse side

underside of the strip, generally coated with a backing coat (see 3.12), but possibly pre-treated only or coated with one of the other systems described in 3.10, 3.11 and 3.13, to fulfil special requirements such as foam or glue adhesion, specially specified friction, etc.

3.9
coating system

combination of coatings either on the top side or on the reverse side of the metal substrate

Note 1 to entry: The name of the coating system derives from the topcoat coating material (see examples in Annex B).

3.10
single layer coating

single coating either with requirements on appearance, formability, corrosion protection, subsequent painting etc., or as a primer with special properties regarding adhesion and corrosion protection for post-painting applications

3.11
multilayer coating

system comprising a primer or a base coat, possibly intermediate coat(s), and a top coat with particular requirements on appearance, formability, corrosion protection, etc.

3.12
backing coat

single coating of any type with no particular requirements for appearance, formability, corrosion protection etc., usually on the reverse side of the coated product

3.13
film coating

organic film applied to a substrate to which an adhesive and, if appropriate, a primer has been applied before-hand

3.14
master coil
parent coil

coil from which products (coil or sheet) are obtained

3.15
order document

document or set of documents agreed between supplier and purchaser at the time of ordering

Note 1 to entry: An order document can be an order of the purchaser confirmed by the supplier or a quotation of the supplier confirmed by the purchaser.

4 Technical conditions for inspection and delivery

4.1 Ordering information

The order document shall specify the product required and shall contain the following information:

- a) the form and type of product:
 - 1) the form of the product (organic coated coil, sheet or strip);
 - 2) the designation of the aluminium or aluminium alloy, in accordance with EN 573-3;
- b) the temper of the material for delivery (degree of hardness or heat treatment condition) in accordance with EN 515 and EN ISO 6892-1;

- c) the dimensions and shape of the product:
- 1) thickness (of the metal substrate);
 - 2) width;
 - 3) length of sheet (in the rolling direction);
 - 4) internal and external diameters of the coil;
 - 5) core size and type.

NOTE Unless otherwise agreed, the length is the largest dimension.

- d) the quantity:
- 1) mass or number of pieces;
- e) the coating system (see examples in Annex B):

- 1) for the top side:
 - i. colour designation (international and/or company code);
 - ii. nominal gloss value;
 - iii. protective strippable film when required;

If the surface is likely to be damaged during transportation, storage, processing or erection, the coil coated material may, on agreement, be supplied with the additional protection of a temporary strippable film. Type, thickness, adhesion properties, formability, tear strength and light fastness should be taken into consideration when choosing protective films. Only certain protective films can be exposed to outdoor weathering, and these only for a limited period.

- 2) for the reverse side:
 - i. whether it is a backing coat or not;
 - ii. colour designation (international and/or company code);
 - iii. nominal gloss value;

- f) the type and the design of embossing, when required;
- g) any requirements for inspection documents;
- h) any special requirements for packing:
- 1) mass per coil and per packing unit;
 - 2) number of sheets per stack;
 - 3) position of coil axis (vertical or horizontal);

- 4) design of pallet;
- 5) direction of winding;

Optional information to be mentioned in the order:

i) the form and type of product:

- 1) the purchaser application;

j) the number of this document, i.e. EN 1396, or a specification number, or, where none exists, the properties agreed between manufacturer and purchaser;

k) the quantity:

- 1) quantity tolerances if required;

l) the coating system:

- 1) for the top side:

- i. special requirements when required such as coat system (single, multiple); type of organic coating (see Table B.1); coating thickness in micrometers, if different from normal (see Table B.1); coating system code; etc.;

- 2) for the reverse side:

- i. special requirements when required such as coat system (single, multiple); type of organic coating (see Table B.1); coating thickness in micrometers, if different from normal (see Table B.1); surface finish if not coated (degreased only, pre-treated etc.); printing of markings; foam adhesion; adhesive bonding, etc.;

m) any special requirements agreed between manufacturer and purchaser:

- 1) marking of products;
- 2) flagging of defects;
- 3) instruction on the position of the top side if other than the normal one (see 3.7);
- 4) other characteristics of the products (see Annex B).

4.2 Requirements

4.2.1 Production and manufacturing processes

Unless otherwise specified in the order, the production and manufacturing processes shall be left to the discretion of the manufacturer. Unless it is explicitly stated in the order no obligation shall be placed on the manufacturer to use the same processes for subsequent and similar orders.

4.2.2 Quality control

The manufacturer shall be responsible for the performance of all inspection and tests required by the relevant European Standard and/or the particular specification, prior to shipment of the product.

If the purchaser wishes to inspect the product at the manufacturer's works, he shall notify the manufacturer at the time of placing the order.

4.2.3 Freedom from defects

The product shall be free from defects prejudicial to its suitable and proper use. Its surface shall be of a uniform appearance, colour and texture and be essentially free of blemishes such as flow lines, streaks, blisters or other imperfections.

Tolerance on surface defects is normally greater for products supplied as coils (as compared to sheets) due to the impossibility of removing defects within coils and this should be taken into account by the purchaser when assessing the product. Limiting samples may be agreed.

Uniformity and aesthetic faults shall be noted when visible. Visible examination shall be done at following distances:

- building façade applications: 5 m for external and 3 m for internal use;
- all other applications: 3 m for external and 2 m for internal use.

4.2.4 Chemical composition

The chemical composition shall comply with the requirements as specified in EN 573-3.

4.2.5 Mechanical properties

The mechanical properties shall be in conformity with those specified in Clause 5 or those agreed upon between the supplier and the purchaser and stated on the order.

4.2.6 Tolerances on shape and dimensions

The tolerances on shape and dimensions specified in EN 485-4 shall apply.

Tolerances on thickness shall only apply to the uncoated (bare) metal substrate. For the tolerances on the organic coating thicknesses see 6.1.

Unless otherwise agreed, the purchaser may reject only those products having dimensions not complying with the specified tolerances.

4.2.7 Coating properties

Property requirements relating to the organic coating are specified in Clause 6. Other requirements shall be agreed by the supplier and the purchaser and stated on the order. Annex C gives some guidelines for such requirements.

4.3 Test procedures

4.3.1 Chemical composition

For chemical composition testing see EN 485-1.

4.3.2 Tensile test

For the selection and preparation of samples and test-pieces see EN 485-1.

Testing shall be carried out according to EN ISO 6892-1, and the following additional requirements:

- the test-piece shall be taken with its length transverse to the rolling direction. For narrow widths (less than 300 mm) testing in the rolling direction is permitted. In this case, testing direction shall be reported and specified;

- the test-piece shall have a reduced section 12,5 mm wide;
- unless otherwise agreed testing shall be carried out on the coated material. The thickness of the metal substrate shall be used for the calculation of the cross-section;
- the elongation shall be measured using an original gauge length of 50 mm.

Testing shall be carried out on at least one test-piece taken from each inspection lot. Furthermore, testing shall be carried out on:

- one test piece taken from each master coil of more than 1 000 kg;
- one test piece taken from every 10 master coils of 500 kg up to 1 000 kg;
- one test piece taken from every 25 master coils of less than 500 kg.

4.3.3 Coating tests

The coating tests shall be carried out either as agreed upon by the manufacturer and the purchaser or in accordance with the following standards:

- coating thickness (when required): EN 13523-1;
- specular gloss: EN 13523-2;
- colour difference: EN 13523-3 and EN 13523-22.

NOTE Instrumental comparison for colour difference (EN 13523-3) does not give reliable values in the case of embossed or textured coatings, metallic or pearlescent pigmented coatings.

The frequency of testing shall be as for the tensile test.

Other tests may be specified. The methods of testing, if other than the ones in the normative references (see Clause 2), the acceptance criteria and the frequency of testing shall be agreed between supplier and purchaser. Guidelines for such specification are set out in Annex C.

4.3.4 Retests

Retests shall be carried out in conformance with EN 485-1.

5 Mechanical properties

Properties shall be in conformance with those specified in Table 1, using the rounding rules set out in Annex A. Properties for alloys and/or tempers not covered in Table 1 shall be agreed between manufacturer and purchaser.

Table 1 — Mechanical properties after coating

Alloy designation	Temper	R_m MPa		$R_{p0,2}$ MPa	A_{50} mm % specified thickness t (mm)		
		min.	max.	min.	$t \leq 0,5$	$0,5 < t \leq 1,5$	$t > 1,5$
EN AW-1050A [Al 99,5]	0	65	95	20	20	22	26
	H42	85	120	65	4	5	6
	H44	100	145	80	3	4	5
	H46	120	160	90	2	3	4
	H48	140	—	120	2	2	3
EN AW-1200 [Al 99,0]	0	75	105	30	19	21	24
	H42	90	135	70	4	5	6
	H44	110	155	90	3	4	5
	H46	130	170	100	2	3	4
	H48	150	—	130	2	2	3
EN AW-3003 [Al Mn1Cu]	0	95	135	35	15	17	17
	H43	130	170	100	4	5	5
	H44	140	185	110	4	4	5
	H45	150	205	130	3	4	4
	H46	165	210	140	2	3	3
	H48	180	220	165	2	2	3
	H49	195	—	190	2	2	2
EN AW-3103 [Al Mn1]	H44	140	180	110	4	4	5
	H46	160	200	140	2	3	3
	H48	180	—	160	2	2	3
EN AW-3004 [Al Mn1Mg1]	H42	185	240	130	4	5	6
	H43	195	235	160	3	4	5
	H44	210	265	180	3	4	4
	H46	230	285	200	3	3	3
	H48	260	—	220	2	3	3
EN AW-3005 [Al Mn1Mg0,5]	0	115	165	45	12	14	16
	H41	130	180	80	7	8	9
	H42	140	195	95	5	5	6
	H44	165	215	135	3	3	4
	H46	185	240	160	2	2	3

Alloy designation	Temper	R_m MPa		$R_{p0,2}$ MPa	A_{50} mm % specified thickness t (mm) min.		
		min.	max.		min.	$t \leq 0,5$	$0,5 < t \leq 1,5$
	H48	210	—	180	1	2	2
EN AW-3104 [Al Mn1Mg1Cu]	H48	240	280	210	4	4	4
	H49	280	—	270	2	2	2
EN AW-3105 [Al Mn0,5Mg0,5]	O	100	150	40	14	15	17
	H42	130	180	105	6	6	7
	H44	150	200	120	3	3	4
	H46	175	225	150	2	2	3
	H48	195	—	170	2	2	2
	H49	200	—	190	2	2	2
EN AW-4017 [Al SiMnMgCu]	H42	145	200	120	2	2	2
EN AW-5005 [Al Mg1(B)]	O	100	145	35	15	19	20
	H42	125	165	80	4	5	6
	H44	145	185	110	3	4	5
	H46	165	205	135	2	3	4
	H48	185	—	160	1	2	3
EN AW-5006 [Al Mg1Mn0,5]	H41	140	190	105	7	7	8
	H48	200	250	180	3	3	3
	H49	200	—	190	2	2	2
EN AW-5010 [Al Mg0,5Mn]	H42	110	150	90	5	5	6
	H44	130	170	100	3	3	4
	H45	140	180	110	2	2	3
	H46	150	190	120	2	2	3
	H48	170	210	140	1	1	2
EN AW-5050 [Al Mg1,5(C)]	H44	170	215	130	3	4	5
	H46	190	235	160	2	3	4
	H48	210	250	180	1	2	3
	H49	240	—	220	1	1	2
EN AW-5251 [Al Mg2]	O	160	200	60	13	14	16
	H44	190	230	120	3	5	6
	H46	210	270	165	3	4	5
	H48	250	—	215	2	3	3

Alloy designation	Temper	R_m MPa		$R_{p0,2}$ MPa	A_{50} mm % specified thickness t (mm) min.		
		min.	max.	min.	$t \leq 0,5$	$0,5 < t \leq 1,5$	$t > 1,5$
EN AW-5052 [Al Mg2,5]	H42	205	260	130	6	7	
	H44	230	280	150	4	5	6
	H46	250	300	180	3	4	5
	H48	—	—	210	3	3	4
EN AW-5754 [Al Mg3]	O	190	240	80	12	14	16
	H41	205	245	125	8	9	10
	H42	220	270	130	7	8	9
	H44	230	280	160	5	5	6
	H46	260	310	190	4	4	5
	H48	280	—	220	3	3	4
EN AW-5182 [Al Mg4,5Mn0,4]	H48	330	—	300	1	1	2
EN AW-6011 [Al Mg0,9Si0,9Cu]	T8	340	—	320	2	2	2
EN AW-6025 [Al Mg2,5SiMnCu]	O	160	220	60	8	10	10
	H41	170	220	100	4	5	5
	H42	180	230	135	2	3	4
	H46	220	260	185	2	3	4
EN AW-8006 [Al Fe1,5Mn]	O	70	—	45	18	18	20
	H42	85	125	75	5	5	6
	H44	90	130	75	2	2	3
EN AW-8011A [Al FeSi(A)]	O	80	120	30	19	21	24
	H44	125	165	100	3	4	5
EN AW-8111	O	75	120	30	20	21	22
	H42	110	155	85	4	4	5

6 Organic coating properties

6.1 Tolerances on thickness

When specified in the order document, the thickness of the organic coating shall meet the tolerances given in Table 2.

These tolerances on the specified coating thickness shall apply to the total organic coating thickness on each relevant side, but not including the strippable film thickness (where applicable).

The measurements shall be carried out on a representative specimen according to EN 13523-1.

The measurements should be carried out on flat samples only (i.e.: not embossed).

For structured surfaces only negative deviation on the average of ten measurements shall be applied.

For powder coatings, maximum allowable deviation from the specified thickness shall be 10 for an average of five measurements and 15 for an individual measurement for all film thicknesses.

Other tolerances as well as the measuring method to be used can be agreed between manufacturer and purchaser; in this case, both pieces of information shall be reported and specified.

Table 2 — Tolerances on total thickness of the organic coating

Dimensions in micrometres

Specified thickness range	$3 < t$	$5 < t \leq 10$	$10 < t \leq 20$	$20 < t \leq 25$	$25 < t \leq 35$	$35 < t \leq 60$	$60 < t \leq 100$	$100 < t \leq 200$	$t > 200$
	≤ 5								0
Maximum allowable negative deviation from the specified thickness: for an average of five measurements	2	2	2	3	3	5	10	15	20
Maximum allowable negative deviation from the specified thickness: for an individual measurement	2	3	4	5	6	8	15	25	40
NOTE 1 Both tolerances are only intended for smooth surfaces. Tolerance for individual measurements does not apply.									
NOTE 2 There are no requirements for backing coat.									
NOTE 3 There are no requirements for the positive deviation.									

6.2 Tolerances on gloss

The test method for measuring specular gloss shall be as specified in EN 13523-2.

NOTE The method does not give reliable values in the case of embossed or textured coatings, metallic or pearlescent pigmented coatings.

The tolerances on gloss measured using a 60° head are specified in Table 3.

These tolerances apply to measurements carried out in accordance with EN 13523-2 using a 60° head, unless otherwise agreed. For gloss values below 10, a 85° head is recommended, where other tolerances may apply.

The measurements should be carried out on flat samples (i.e.: not embossed).

Other values may be agreed between supplier and purchaser.

Test method and gloss tolerances for textured finishes should be agreed between supplier and purchaser.

Table 3 — Tolerances on gloss

Values in gloss units

Gloss unit range	Tolerances on nominal gloss	Maximum variation within one supply	Gloss type
≤ 10	±2	±1	matt
> 10 ≤ 20	±4	±2	low gloss
> 20 ≤ 40	±5	±3	satin
> 40 ≤ 60	±7	±5	semi-gloss
> 60 ≤ 80	±8	±7	gloss
> 80	Minimum gloss 80		high gloss

6.3 Tolerances on colour

The colour shall match visually the colour specified. If necessary, appropriate colour tolerances should be agreed in advance. Recommendations for the evaluation are specified in Annex C.

7 Inspection documents

Inspection documents shall be issued in accordance with EN 485-1.

8 Marking

Unless otherwise agreed at the time of ordering, the following minimum marking requirements shall apply:


- name or mark of the manufacturer;
- alloy and temper designation for the substrate;
- information on the coating on each surface;
- order number;
- ordered dimensions;
- production batch number and mass.

Each of these items shall be given on a label, which is to be attached to every coil or pack.

9 Packing

The packing requirements shall be agreed between manufacturer and purchaser at the time of ordering.

For coils packed eye to the sky — when observed from the top — the direction of winding is specified as clock-wise or anti-clockwise according to the following sketch (Figure 1):



a) Clockwise



b) Anti-clockwise

Figure 1 — Direction of winding

10 Arbitration tests

In cases of dispute concerning conformity with the requirements of this document or specification cited on the order, before rejecting the products, testing and examination shall be carried out by an arbitrator chosen by mutual agreement between manufacturer and purchaser.

The arbitrator's decision shall be final.

Annex A
(normative)

Rules for rounding

In recording test results, the number representing the result of a test to determine a given property shall be expressed to the same number of decimal places as the corresponding number in this document.

The following rounding rules shall be used for determination of compliance with this document:

- a) when the figure immediately after the last figure to be retained is less than 5, the last figure to be retained remains unchanged;
- b) when the figure immediately after the last figure to be retained is greater than 5, or equal to 5 and followed by at least one figure other than zero, the last figure to be retained is increased by one;
- c) when the figure immediately after the last figure to be retained is equal to 5 and followed by zeros only, the last figure to be retained remains unchanged if even and is increased by one if odd.

The results of determinations of dimensions (length, width, thickness etc.) and shape (squaring, cambering, straightness, flatness etc.) shall not be rounded. These shall comply with the specification in the relevant European standard, taking into account permissible tolerances also given in that European standard.

Annex B
(informative)

Examples of coating systems

EXAMPLE 1 Topside: Two coat system, PVDF, colour xxxx, gloss xxx units, coating thickness xxx μm , with protective strippable film.

Reverse side: Single coat system requiring PU foam adhesion, coating thickness approx. xxx μm .

EXAMPLE 2 Topside: Two coat system, Polyester (PT), colour xxxx, gloss xxx units, coating thickness xxx μm , with protective strippable film.

Reverse side: Two coat system, Polyester (PT), colour xxxx, gloss xxx units, coating thickness xxx μm .

EXAMPLE 3 Topside: Single coat system, Epoxy (EP), colour xxxx, gloss xxx units, coating thickness xxx μm .

Reverse side: Pre-treated only.

EXAMPLE 4 Topside: Laminated with PVC-film, colour xxxx, gloss xxx units, film thickness xxx μm .

Reverse side: Backing coat, approx. xxx μm .

EXAMPLE 5 Topside: Two coat system, Polyester (PT), with stripes, stripe code n° xxxx (drawing N.), colour of base coat xxxx, colour of stripe 1 xxxx, colour of stripe 2 xxxx, gloss xxx units, coating thickness (base coat) xxx μm , coating thickness (stripes) xxx μm .

Reverse side: Backing coat, approx. xxx μm .

Table B.1 — Symbol and typical thickness or thickness ranges of the more common coating materials (for information only)

Dimensions in micrometres		
Coating material	Symbol ^a	Typical thickness or thickness ranges ^b
Liquid coatings		
Acrylic	AY	20
Alkyd	AK	15
Epoxy	EP	5
Fluoropolymer	FEVE	10 to 40
Polyamide (PA) modified systems	PUR-PA and PT-PA	20 to 30
Polyesters	PE	10 to 20
Polyurethane	PUR	20
Polyurethane adhesives	PUR(A)	6
Polyvinylidene fluoride	PVDF	20 to 40
Silicone modified polyester	PT-SI	20
Powder coatings		
Polyester	SP	50 to 80
Epoxy	EP	50 to 80
Laminated films ^c		
Polyvinyl chloride	PVC(F)	> 100
Polyvinyl fluoride	PVF(F)	38
Polyester	PET	< 150
^a The symbols correspond broadly to those in EN ISO 1043-1 or were chosen by analogy. ^b The typical thickness values relate to the individual coats (excluding primer and adhesive coatings). ^c Excluding adhesive coating thickness of approximately 10 µm.		

Annex C
(informative)

Guidelines for organic coatings

C.1 General

Coil coated products should comply with the relevant requirements of this annex when agreed between supplier and purchaser and stated on the order.

C.2 to C.5 can be used for lot acceptance if so agreed.

C.6.2 to C.6.5 are only intended for surveillance purpose. The frequency of the relevant test is left to the discretion of the manufacturer, who should maintain records of the lots so tested and make them available for examination at the manufacturer's facility.

C.2 Colour

The colour should be measured according to EN 13523-3 and should not differ from the agreed standard by:

White and pastel colours	$\Delta E \leq 1$ (where white and pastel colours are specified as $L^* > 80$ and $C^*(a,b) < 10$).
Other colours	$\Delta E \leq 2$

Illuminants and geometry should be declared. For specific colours, other tolerances can be agreed at the time of inquiry and order.

Within one supply the colour difference between extremes should not exceed $\Delta E 0,7$ CIELAB unit.

These figures are for guidance only and are not appropriate for all colours. Therefore, specific numerical values should be set when necessary.

The measurements should be executed on a mutually agreed colour measurement device. This does not apply to metallic paint finishes, textured coatings and embossed surfaces.

The colour should be evaluated visually according to EN 13523-22.

C.3 Flexibility

Flexibility of the organic coating is assessed by subjecting the material to a bend test. The test should be carried out on a material at ambient temperature.

The bend test should be carried out according to EN 13523-7 in the rolling direction. If the transverse direction is used it should be specified in the report.

As an alternative to the devices covered in EN 13523-7 the following method may be used to carry out the bending (see also Figure C.1):

- the test piece (at least 250 mm × 30 mm) is bent (at 1 cm from one extremity) over an angle of approximately 100° by hand or by any other convenient means;
- the bent test-piece is then pressed, using a vice or a hydraulic press, until the two faces come into contact. This constitutes the "OT" bend;

- if the bent area shows cracks with apparent underlying metal, a second bend is carried out by folding the test-piece over the first bend and then pressing it using the vice or press. This constitutes the “0,5T” bend;
- this procedure is continued until a crack free bend is obtained;
- in case of dispute the test should be carried out at a temperature of 23 ± 2 °C and at a relative humidity of $50 \% \pm 5 \%$.

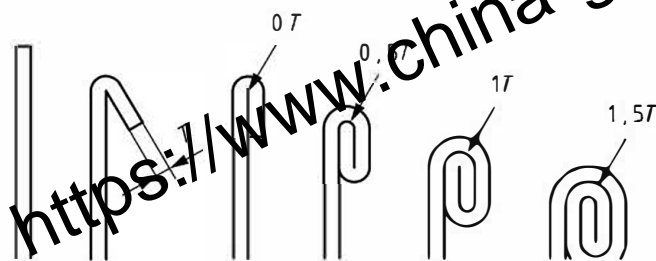


Figure C.1 — Bending values

The frequency of testing should be as for the tensile test.

Bending values should not exceed 3T, unless otherwise specified or agreed between supplier and purchaser.

Measured bend radii are governed by the choice of metal substrate, temper, thickness and coating material. Therefore, when limit values are required, these should be agreed between supplier and purchaser and stated on the order in accordance with the shape and folds of the finished product.

C.4 Adhesion

C.4.1 Adhesion of the organic coating is assessed by evaluating the coating surface, after deformation, in specified conditions, of a specimen previously cross-hatched with a cutting tool. Cross-hatching should be carried out according to EN 13523-6. The specimen should then be deformed using one of the following methods as appropriate:

- method 1: liquid coating from which the film thickness is up to 50 μm may be reverse impact tested in accordance with either EN 13523-5, ISO 6272-1 or ISO 6272-2, using the maximum indentation energy that will not rupture the substrate. Tested with tape, there should be no loss of adhesion of the organic coating. Cracking of the paint film should not be considered as a cause for rejection.
- method 2: coatings should be tested in accordance with EN 13523-6 followed by EN ISO 1520, noting the following:
 - cross-hatching should comprise two parallel cuts made 5 mm apart, together with two additional similar cuts made at right angles to form a central 5 mm \times 5 mm central square. The cuts should just reach the metal, and each cut should measure at least 50 mm in length;
 - **for coatings greater than or equal to 60 μm thickness.** After indentation, an attempt is made to pull the strips away from the substrate in each of the four directions, starting from the central square. The ends of the strips are lifted with a knife, then pulled with pincers. The peeling is observed and expressed in percentage of the distance between the top and the base of the dome. If ageing is carried out, express the adhesion as a percentage of peeling for the ageing period;

- **for coating less than 60 µm thickness.** Remove two complete laps from a reel of adhesive tape and discard. Remove an additional length at a steady rate and cut a piece approximately 75 mm long. Place the centre of the tape over the lattice in a direction parallel to one set of cuts and smooth the tape into place over the area of the lattice and for a distance of at least 20 mm beyond. To ensure good contact with the coating, rub the tape firmly with a fingertip. The colour of the coating seen through the tape is a useful indication of overall contact. Within 1 min of applying the tape, remove the tape by holding the free end and pulling it off steadily in 0,5 s to 1 s at an angle that is as close as possible to 60° (see also EN ISO 2409:2020, A.6) from the panel. Assess the degree of adhesion after removal of the adhesive tape;
- for the maximum indentation depth that will not rupture the substrate, peeling should not exceed 75 %.

C.4.2 Alternatively, all coatings may be subjected to one of the bend tests described in C.3. Tested with tape, no loss of adhesion is allowed for 2 m bends (radius of the mandrel equal to twice the substrate thickness).

C.5 Pencil hardness

When tested in accordance with EN 13523-4, the hardest pencil that does not rupture the paint should be at least F.

This test is only valid for smooth paints and do not apply for film thicknesses over 50 µm.

C.6 Durability of the organic coating

C.6.1 General

C.6.1.1 The requirements proposed as guidelines in the present section, i.e. C.6, take into account the envisaged application which will affect the choice of the product to be ordered. Accordingly, provision is made for four categories of coil coated metal products as follows:

- category 1: pre-painted metal product intended only for further painting after fabrication;
- category 2: pre-painted metal product suitable for the following interior applications:
 - a) dry and wet non-corrosive areas;
 - b) wet corrosive areas;
- category 3: pre-painted metal product suitable for the following exterior applications:
 - c) rural; or urban or light industrial (or mild marine);
 - d) tropical (high temperatures, high humidity);
 - e) high U.V (ultraviolet);
- category 4: pre-painted metal product suitable for the following applications:
 - f) severe industrial — extreme conditions;

- g) very severe coastal marine (less than 3 000 m from the sea, depending also on the landscape);
- h) high U.V plus severe conditions (tropical and marine).

C.6.1.2 Testing may include actual outdoor exposure tests (see C.6.2 and C.6.3) or accelerated laboratory tests (see C.6.4, C.6.5 and C.6.6).

In the case of new products, the expected performance is to be as stated in Tables C.2 and C.3 (for natural UV radiation). In the interim, the performance should be evaluated using accelerated tests.

For the purpose of these tests the expected resistance of the coating system to corrosion is expressed by means of indices varying from 1 to 3 and the resistance to UV exposure by means of categories R_{UV2} , R_{UV3} , R_{UV4} and R_{UV5} , specified as follows:

- 1 and R_{UV2} : low resistance;
- 2 and R_{UV3} : medium resistance;
- 3 and R_{UV4}/R_{UV5} : high resistance.

C.6.1.3 Outdoor exposure tests are carried out by the manufacturers in a variety of sites representing marine, industrial, urban or rural environments or combinations thereof. Panel preparation and method of exposure, although essentially similar, can vary from one manufacturer to another. These tests should be carried out in accordance with EN 13523-19 and EN 13523-21.

The expected performances specified in C.6.2 and C.6.3 apply to panels tested according to these methods.

C.6.1.4 It is to be noted that the performance of the coating system has to be specific to the environment for which it is intended and one or more of the aspects quantified (UV and/or corrosion) are usually required. Table C.1 gives, for each category specified in C.6.1.1, recommended corrosion indices and UV resistance categories which the coating systems should present.

Table C.1 — Recommendations for selection of coil coated material

Category	End use environment	Corrosion resistance index	UV resistance category
1	Pre-painted metal product intended only for further painting after fabrication	—	—
2	Pre-painted metal product suitable for the following interior applications:		
2a	Dry and wet non-corrosive areas	1	R_{uv2}
2b	Wet corrosive areas	3	R_{uv2}
3	Pre-painted metal product suitable for the following exterior applications:		
3a	Rural or urban light industrial (no light marine)	2	R_{uv3}
3b	Tropical (high temperature, high humidity)	3	R_{uv4}
3c	High UV	2	R_{uv4}/R_{uv5}
4	Pre-painted metal product suitable for the following applications:		
4a	Severe industrial — extreme conditions	3	R_{uv3}
4b	Very severe costal marine (less than 3 000 m from the sea, depending also on the landscape)	3	R_{uv3}
4c	High UV plus severe conditions	3	R_{uv4}/R_{uv5}
<p>NOTE 1 Corrosion indices and UV resistance categories are rated on the following scale: 1, R_{uv2} = Low 2, R_{uv3} = Medium 3, R_{uv4}/R_{uv5} = High</p> <p>NOTE 2 Coatings that do not fulfil the requirements of R_{uv2} classification are classified as R_{uv1}.</p>			

C.6.2 Corrosion resistance (outdoor exposure)

Testing should be carried out according to EN 13523-19 on panels exposed at 90° facing the North. Observations should be recorded in line with the formats detailed in EN 13523-21.

For aluminium, examples of C3 exposure sites in Europe that may be used are Hoek van Holland (The Netherlands), Brest (France), and Sines (Portugal). Bohus-Malmön Kvarnvik in Sweden is an example of an C3/C4 site. Other sites complying with ISO 9223 may be selected. Types 1, 2 and 3 specimens are specified in EN 13523-19 and the method for their evaluation in EN 13523-21. Type 2 and 3 specimens are exposed on a corrosion site whose corrosivity is related to the corrosion resistance category intended to be obtained for a certain product.

The expected average under creep on the front side of the panel should not exceed the values specified in Table C.2. Attacked surface should not exceed 5 % of total exposed surface.

Table C.2 — Expected performance of a panel exposed at a C3 site

Exposure duration	1 year		3 years	
Corrosion resistance index	2	3	2	3
Average under creep	≤ 2 mm	≤ 1 mm	≤ 4 mm	≤ 2 mm

C.6.3 UV resistance

C.6.3.1 General

Colour change and retained gloss should be evaluated on correctly cleaned specimens. The colour change during UV exposure should be measured according to EN 13523-3 using the CIE L*a*b* units. The results depend on the colour measurement set up and the measurement conditions should then be detailed when giving a colour change value. The retained gloss (RG) should be measured according to EN 13523-2.

The cleaning conditions may be changed upon agreement at the time of enquiry and order.

For natural exterior exposure, the test duration is 2 years for all UV resistance categories R_{uv2} , R_{uv3} and R_{uv4} and 4 years for UV resistance category R_{uv5} . The relationship between UV categories indicating the level of UV radiation in the environment and geographical areas is given in Table C.3 for guidance.

Exposure sites located in Lisbon (Portugal) and Sanary-sur-Mer (France) meet the requirements of this specification. Other sites with the same minimum cumulative solar energy can also be used.

Type 1, 2 and 3 specimens are specified in EN 13523-19. Type 1 specimens are exposed in a site providing at least 4 500 MJ/m²/year of cumulative solar energy measured horizontally. See C.6.4 and C.6.5 for testing conditions. The aspect of Type 1 specimens should not exhibit variations more than those reported in Table C.3 for UV resistance categories R_{uv2} , R_{uv3} , R_{uv4} and R_{uv5} .

Table C.3 — Requirements for the UV resistance for natural and artificial testing conditions

Requirements	UV resistance category			
	R_{uv2}	R_{uv3}	R_{uv4}	R_{uv5}
Test duration, natural exposure (years)	2	2	2	
Test duration ^e , artificial UV radiation (h)	2 000	2 000	2 000	2 000
Maximum colour change ΔE^* ^a before and after the test (CIELab units)	5	3	2 ^d	3 ^c 2 ^d
Minimum retained gloss after the test (RG ^b), %	30	30 ^c 80 ^d	80	80
<p>^a The ΔE^* value is not applicable for saturated and other special colours such as metallics and pearlescent. In that case the colour change verification method and its acceptance value should be agreed at the time of enquiry and order.</p> <p>^b The retained gloss (RG) is the ratio of the final gloss value, given in percent. The RG requirement is not applicable to matt coating systems as specified in Table 3.</p> <p>^c Natural UV radiation.</p> <p>^d Artificial UV radiation.</p> <p>^e The UV category can be granted after an artificial UV radiation test but it should be validated after completion of natural ageing in an accredited outdoor exposure site.</p>				

C.6.3.2 Natural outdoor UV radiation resistance tests

The exposure site should provide at least 4 500 MJ/m²/year of cumulative solar energy measured horizontally, with examples regarding the exposures for the different UV resistance categories provided in Table C.4. Specimen cleaning conditions can influence test results significantly. Colour change and retained gloss should be evaluated on correctly cleaned specimens. The cleaning conditions may be changed upon agreement at the time of enquiry and order. Lisbon (PT) is an example of a UV radiation exposure site. Other sites with the same minimum cumulative solar energy may be selected as well.

The test duration is 2 years for all UV resistance categories R_{uv2} , R_{uv3} and R_{uv4} and 4 years for UV resistance category R_{uv5} .

Table C.4 — Examples of exposures for the different UV resistance categories

UV Resistance category	Example
R_{uv1}	Reverse coating of exterior elements.
R_{uv2}	Regions located north of about latitude 45° N, with an altitude not greater than 900 m.
R_{uv3}	Regions located south of about latitude 45° N and north of about latitude 37° N, with an altitude not greater than 900 m.
R_{uv4} and R_{uv5}	Regions located south of about latitude 37° N. Every region with an altitude greater than 900 m.
<p>NOTE 1 Examples given are of general guidance since local conditions in relation with sunshine hours and UV radiation can vary considerably even in a small geographical area.</p> <p>NOTE 2 For buildings located next to the sea or large lakes or areas covered with snow, UV radiation can be increased due to reflection from the corresponding surfaces.</p>	

C.6.3.3 UV radiation resistance (accelerated test)

UV radiation resistance tests should be carried out in accordance with EN 13523-10.

UV resistance tests should not be carried out on coatings of UV resistance category R_{uv1} .

The artificial ageing test under combined action of both UV radiation and condensation is carried out for coating system categories R_{uv2} , R_{uv3} , R_{uv4} and R_{uv5} by using UVA-340 lamps. The test duration is 2 000 hours (250 cycles) for all categories except R_{uv5} where the test duration is 4 000 hours. When other radiation sources are used (such as UVB-313 or Xenon), tolerances might differ from the values stated in Table C.3 and should be agreed at the time of enquiry then stated in order.

Artificial weathering or exposure to artificial radiation of coatings in fluorescent UV-condensation type machines is carried out in order to establish after a certain radiation exposure or mutually agreed total number of operation hours, the degree of a change of a property or properties. The properties of the exposed coatings should be compared with those of unexposed coatings, prepared from the same coating materials under identical conditions or with coatings whose degradation properties are known. These properties should be evaluated by criteria agreed in advance between the interested parties, these criteria usually being of a subjective nature.

During natural weathering, global radiation and wet conditions are be considered as essential for the ageing of coatings. Therefore, the use of the artificial weathering apparatus specified in this document should be about simulating exposure to UV light and moisture.

During natural weathering, global radiation and wet conditions are considered as essential for the ageing of coatings. Therefore, the use of the artificial weathering apparatus specified in this document should be about simulating exposure to UV light and moisture.

The results obtained by the use of this method do not necessarily relate directly with results obtained under natural exposure conditions. The relationship between these results should be established before the method can be used to predict performance.

Other test methods may be agreed at the time of enquiry then to be stated in order.

C.6.4 Humidity and water immersion resistance (accelerated tests)

When tested for 1 000 h in accordance with EN 13523-25, or for an appropriate duration at 40 °C in accordance with EN 13523-9, any blistering should be less than blister size B2 (S2) (EN ISO 4628-2).

C.6.5 Acetic acid salt spray fog resistance (accelerated corrosion test)

When tested for 500 h in accordance with EN 13523-8 the average under creep should not exceed the values specified in Table C.5.

Table C.5 — Maximum values for average under creep and face blistering after accelerated corrosion testing

Test criterion	Testing time h	Corrosion resistance index		
		1	2	3
Under creep corrosion mm	500	4	2	1
	1 000	—	3	2
Face blistering (EN ISO 4628-2)	500	none		
	1 000	B2 (S2)		

NOTE When tested in the neutral salt spray fog, according to EN ISO 9227, coil coated aluminium and aluminium alloys are almost unaffected.

Sample edge protection in the acetic acid salt spray test is optional. If the influence of the electrochemical behaviour of exposed aluminium at cut-edges is to be reduced at least three of the four cut edges on the sample should be protected.

C.6.6 Filiform corrosion test, FFC (accelerated corrosion test)

When tested for 500 h in accordance with EN ISO 4623-2 the average filiform corrosion should not exceed the values specified in Table C.6.

Table C.6 — Maximum values for average filiform corrosion and after accelerated corrosion testing

Test criterion	Testing time h	Corrosion resistance index		
		1	2	3
Under filiform corrosion mm	500	L4/M	L2/M2	L1/M1
	1 000	—	L3/M3	L2/M2

NOTE 1 L = longest filament, M = most frequent filament.

NOTE 2 Filiform corrosion (FFC) test (EN ISO 4623-2) is complementary to the Acetic acid salt spray.

Annex D (informative)

Guidelines for storage and subsequent processing

D.1 Storage

If possible, storage should be in dry or air-conditioned buildings. Generally, the products should be protected from damp and stored in a dry condition.

When packs are stacked, the height of the stack should be limited to prevent pressure marking of the coating. Coils should never be placed or stored on bare ground, but should be supported by wooden blocks or protective mats.

Any unevenness in solid matter on the surface of the storage areas that could produce pressure points or dents in the sheet should be avoided as, under certain circumstances, they could make the outer laps unusable. Coils with horizontal axis should not be stored on top of each other.

Sheets should be removed from the packing by careful lifting, not by sliding, so as to avoid scratches caused by burrs - often invisible - or by dust and dirt (e.g. pneumatic sheet lifters, rubber suction pads etc. should be used).

D.2 General instructions for processing

Organic coated flat products already have their finished surface in the delivered condition.

Pressing tools used in processing should therefore be suited to the material, and a smooth clean surface is essential. Polished and hard chrome plated tools are recommended.

Manufacturer advice should be sought when processing flat products with protective films.

Where there are particular requirements on flatness it is recommended that a levelling machine be used, as in the processing of uncoated flat products.

D.3 Forming

Organic coated flat products are suitable for forming by most known methods e.g. roll forming, bending, press forming and deep drawing provided that an appropriate combination of substrate and coating are selected and that attention is paid to tool design.

Forming should be carried out on a material at temperature over 20 °C wherever possible.

D.4 Cutting

Organic coated flat products can generally be cut, punched and perforated in the same manner as uncoated flat products, but very high processing speeds should be avoided. Care should be taken to ensure setting of tool clearance. Materials with thick coatings (PVC plastisols and films) should be cut from the bottom side. Any swarf from cutting should be carefully removed from the surface before further treatment.

In case of using steel, copper and aluminium in the same machine, it is recommended to clean the machine before using the aluminium.

D.5 Joining

The common mechanical joining methods, such as the use of screws, rivets, spring fasteners and lock seaming, are suitable. Fasteners should be corrosion protected.

Organic flat coated products can, in principle, be adhesive bonded to each other and to other materials if selected adhesives are used.

Under certain conditions, organic coated flat products can be welded by various methods. The manufacturer advice should be sought.

The physical properties of the product should not be affected by the joining.

D.6 Cleaning

Only water based mild cleaning agents should be used for cleaning organic coated flat products. The manufacturer advice should be sought for other cleaning agents especially solvents.

Dirt retention can be expressed as the ease with which the product is cleaned according to the paragraph below.

Regular cleaning of organic coatings will maintain the surface in a satisfactory state. Cleaning should be carried out at least once a year or when the appearance has become unsightly or when deposits of atmospheric pollution or matter washed down from building surfaces are apparent. The finishes should be washed with water containing a mild detergent, as recommended by the supplier. Harsh scrubbing or the use of abrasive or solvent cleaners, which will change the finish should be avoided. The cleaning has to be carried out from top to bottom.

D.7 Temporary protective films

The utility of a protective film thus depends essentially on the protection required and the processing operations to be performed. The thickness of the protective film (between 35 µm and 100 µm transparent or colours film and UV resistance Black/White) should be agreed upon at the moment of enquiry and order.

All protective films applied to the products should be removed immediately following the installation of the products, unless otherwise specified by the vendor.

Bibliography

- [1] EN 3665, *Aerospace series - Test methods for paints and varnishes - Filiform corrosion resistance test on aluminium alloys*
- [2] EN 13523-4, *Coil coated metals - Test methods - Part 4: Pencil hardness*
- [3] EN 13523-5, *Coil coated metals - Test methods - Part 5: Resistance to rapid deformation (impact test)*
- [4] EN 13523-6, *Coil coated metals - Test methods - Part 6: Adhesion after indentation (cupping test)*
- [5] EN 13523-7, *Coil coated metals - Test methods - Part 7: Resistance to cracking on bending (T-bend test)*
- [6] EN 13523-8, *Coil coated metals - Test methods - Part 8: Resistance to salt spray (fog)*
- [7] EN 13523-9, *Coil coated metals - Test methods - Part 9: Resistance to water immersion*
- [8] EN 13523-10, *Coil coated metals - Test methods - Part 10: Resistance to fluorescent UV radiation and water condensation*
- [9] EN 13523-19, *Coil coated metals - Test methods - Part 19: Panel design and method of atmospheric exposure testing*
- [10] EN 13523-21, *Coil coated metals - Test methods - Part 21: Evaluation of outdoor exposed panels*
- [11] EN 13523-25, *Coil coated metals - Test methods - Part 25: Resistance to humidity*
- [12] EN ISO 1043-1, *Plastics - Symbols and abbreviated terms - Part 1: Basic polymers and their special characteristics (ISO 1043-1)*
- [13] EN ISO 1519, *Paints and varnishes - Bend test (cylindrical mandrel) (ISO 1519)*
- [14] EN ISO 1520, *Paints and varnishes - Cupping test (ISO 1520)*
- [15] EN ISO 2409:2020, *Paints and varnishes - Cross-cut test (ISO 2409:2020)*
- [16] EN ISO 4623-2, *Paints and varnishes - Determination of resistance to filiform corrosion - Part 2: Aluminium substrates (ISO 4623-2)*
- [17] EN ISO 4628-2, *Paints and varnishes - Evaluation of degradation of coatings - Designation of quantity and size of defects, and of intensity of uniform changes in appearance - Part 2: Assessment of degree of blistering (ISO 4628-2)*
- [18] EN ISO 4628-4, *Paints and varnishes - Evaluation of degradation of coatings - Designation of quantity and size of defects, and of intensity of uniform changes in appearance - Part 4: Assessment of degree of cracking (ISO 4628-4)*
- [19] EN ISO 4628-5, *Paints and varnishes - Evaluation of quantity and size of defects, and of intensity of uniform changes in appearance - Part 5: Assessment of degree of flaking (ISO 4628-5)*

- [20] EN ISO 4628-6, *Paints and varnishes - Evaluation of degradation of coatings - Designation of quantity and size of defects, and of intensity of uniform changes in appearance - Part 6: Assessment of degree of chalking by tape method (ISO 4628-6)*
- [21] EN ISO 6270-1, *Paints and varnishes - Determination of resistance to humidity - Part 1: Condensation (single-sided exposure) (ISO 6270-1)*
- [22] EN ISO 6272-1, *Paints and varnishes - Rapid-deformation (impact resistance) tests - Part 1: Falling-weight test, large-area indenter (ISO 6272-1)*
- [23] EN ISO 6272-2, *Paints and varnishes - Rapid-deformation (impact resistance) tests - Part 2: Falling-weight test, small-area indenter (ISO 6272-2)*
- [24] EN ISO 9223, *Corrosion of metals and alloys - Corrosivity of atmospheres - Classification, determination and estimation (ISO 9223)*
- [25] EN ISO 9227, *Corrosion tests in artificial atmospheres - Salt spray tests (ISO 9227)*
- [26] ASTM D 660, *Standard Test Method for Evaluating Degree of Checking of Exterior Paints*
- [27] EN 541, *Aluminium and aluminium alloys - Rolled products for cans, closures and lids - Specifications*

<https://www.china-gauges.com/>

<https://www.china-gauges.com/>

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than one device provided that it is accessible by the sole named user only and that only one copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than one copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright and Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email cservices@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email: cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK