



BSI Standards Publication

<https://www.china-gauges.com/>

Copper and copper alloys — Wire for general purposes

National foreword

This British Standard is the UK implementation of EN 12166:2024. It supersedes BS EN 12166:2016, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee NFE/34, Copper and copper alloys.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

This publication has been prepared under a mandate given to the European Standards Organizations by the European Commission and the European Free Trade Association. It is intended to support requirements of the EU legislation detailed in the European Foreword. A European Annex, usually Annex ZA or ZZ, describes how this publication relates to that EU legislation.

For the Great Britain market (England, Scotland and Wales), if UK Government has designated this publication for conformity with UKCA marking (or similar) legislation, it may contain an additional National Annex. Where such a National Annex exists, it shows the correlation between this publication and the relevant UK legislation. If there is no National Annex of this kind, the relevant Annex ZA or ZZ in the body of the European text will indicate the relationship to UK regulation applicable in Great Britain. References to EU legislation may need to be read in accordance with the UK designation and the applicable UK law. Further information on designated standards can be found at www.bsigroup.com/standardsandregulation.

For the Northern Ireland market, UK law will continue to implement relevant EU law subject to periodic confirmation. Therefore Annex ZA/ZZ in the European text, and references to EU legislation, are still valid for this market.

UK Government is responsible for legislation. For information on legislation and policies relating to that legislation, consult the relevant pages of www.gov.uk.

© The British Standards Institution 2024
Published by BSI Standards Limited 2024

ISBN 978 0 539 20213 7

ICS 77.150.30

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 October 2024.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

<https://www.china-gauges.com/>

<https://www.china-gauges.com/>

EUROPEAN STANDARD

EN 12166

NORME EUROPÉENNE

EUROPÄISCHE NORM

October 2024

ICS 77.150.30

Supersedes EN 12166:2016

English Version

Copper and copper alloys - Wire for general purposes

Cuivre et alliages de cuivre - Fils pour usages généraux

Kupfer und Kupferlegierungen - Drähte zur
allgemeinen Verwendung

This European Standard was approved by CEN on 5 August 2024.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Rue de la Science 23, B-1040 Brussels

Contents

European foreword.....	3
Introduction	5
1 Scope.....	6
2 Normative references.....	6
3 Terms and definitions	6
4 Designation.....	7
4.1 Material.....	7
4.1.1 General.....	7
4.1.2 Symbol.....	7
4.1.3 Number	7
4.2 Material condition	7
4.3 Product.....	7
5 Ordering information	9
6 Requirements	11
6.1 Composition	11
6.2 Mechanical properties.....	11
6.3 Grain size.....	11
6.4 Dimensions and tolerances	11
6.4.1 Diameter or width across-flats.....	11
6.4.2 Shape tolerances	11
6.4.3 Corner and edge geometry (wire with square and rectangular cross-section only).....	11
6.5 Joins.....	12
6.6 Surface quality.....	12
6.7 Internal inclusion.....	12
7 Sampling.....	13
7.1 General.....	13
7.2 Analysis.....	13
7.3 Tensile, hardness and grain size tests.....	13
8 Test methods	13
8.1 Analysis.....	13
8.2 Tensile test	13
8.3 Hardness test.....	14
8.4 Estimation of average grain size.....	14
8.5 Retests.....	14
8.6 Rounding of results	15
9 Certificate of compliance and inspection documentation.....	15
9.1 Certificate of compliance.....	15
9.2 Inspection documentation.....	15
10 Marking, packaging, labelling.....	15
Annex A (informative) Position of wire cross-section within a coil, reel, spool or drum	45
Annex ZA (informative) Relationship between this European Standard and the essential requirements of Directive 2014/68/EU (Pressure equipment Directive) aimed to be covered.....	47
Bibliography.....	48

<https://www.china-gauges.com/>

European foreword

This document (EN 12166:2024) has been prepared by Technical Committee CEN/TC 133 "Copper and copper alloys", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by April 2025, and conflicting national standards shall be withdrawn at the latest by April 2025.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN 12166:2016.

In comparison with EN 12166:2016, the following significant technical changes were made:

- a) Modification of the definition of diameter or width across-flats in 6.4.1;
- b) Modification of 6.4.2 with the introduction of 6.4.2.1 Round wire and 6.4.2.2 Wire with square or regular cross-section;
- c) Introduction of eddy current test parameters in 6.6;
- d) Introduction of 6.7 Internal inclusion;
- e) Addition of CuPb1P (CW113C) in Table 1 and Table 7;
- f) Addition of CuSn5 (CW451K) in Table 3 and Table 9;
- g) Addition of a new alloy CuZn36Si1P (CW726R) in Table 6 and Table 12;
- h) Introduction in the chemical composition Tables of a footnote to explain the meaning of elements for which no upper and lower limits are specified;
- i) Modification of the chemical composition of CuZn39Pb3 (CW614N) and CuZn40Pb2 (CW617N) in Table 5;
- j) Addition of a new alloy CuZn40Pb1 (CW627N) in Table 5 and Table 11;
- k) Addition of Table 19;
- l) Addition of Annex ZA.

This document is one of a series of European Standards for the copper and copper alloy products rod, wire, profile and forgings. Other products are specified as follows:

- EN 12163, *Copper and copper alloys — Rod for general purposes*;
- EN 12164, *Copper and copper alloys — Rod for free machining purposes*;
- EN 12165, *Copper and copper alloys — Wrought and unwrought forging stock*;
- EN 12167, *Copper and copper alloys — Profiles and bars for general purposes*;

- EN 12168, *Copper and copper alloys — Hollow rod for free machining purposes*;
- EN 13601, *Copper and copper alloys — Copper rod, bar and wire for general electrical purposes*;
- EN 13602, *Copper and copper alloys — Drawn, round copper wire for the manufacture of electrical conductors*;
- EN 13605, *Copper and copper alloys — Copper profiles and profiled wire for electrical purposes*.

This document has been prepared under a standardization request addressed to CEN by the European Commission. The Standing Committee of the EFTA States subsequently approves these requests for its Member States.

For the relationship with EU Legislation, see informative Annex ZA, which is an integral part of this document.

Any feedback and questions on this document should be directed to the users' national standards body. A complete listing of these bodies can be found on the CEN website.

According to the CEN-CENELEC Internal Regulations, the national standards organisations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Republic of North Macedonia, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Türkiye and the United Kingdom.

Introduction

The European Committee for Standardization (CEN) draws attention to the fact that it is claimed that compliance with this document may involve the use of a patent concerning the alloy CuZn36Si1P (CW726R) given in 6.1.

CEN takes no position concerning the evidence, validity and scope of this patent right.

The holder of this patent right has ensured the CEN that he is willing to negotiate licenses either free of charge or under reasonable and non-discriminatory terms and conditions with applicants throughout the world. In this respect, the statement of the holder of this patent right is registered with CEN.

Information may be obtained from:

- For CuZn36Si1P (CW726R) information may be obtained from:

Luvata Oy
Kuparitie 5
28330 Pori
FINLAND

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights other than those identified above. CEN shall not be held responsible for identifying any or all such patent rights.

CEN and CENELEC maintain online lists of patents relevant to their standards. Users are encouraged to consult the lists for the most up to date information concerning patents (<https://www.cencenelec.eu/european-standardization/ipr-and-patents/patents/>).

Due to developing legislation, the composition of a material may be restricted to the composition specified in this European Standard with respect to individual uses (e.g. for the use in contact with drinking water in some Member States of the European Union). These individual restrictions are not part of this European Standard. Nevertheless, for materials for which traditional and major uses are affected, these restrictions are indicated. The absence of an indication, however, does not imply that the material can be used in any application without any legal restriction.

1 Scope

This document specifies the composition, property requirements and dimensional tolerances for copper alloy wire, finally produced by drawing, rolling or extruding, intended for general purposes, spring and fastener manufacturing applications.

The sampling procedures and the methods of test for verification of conformity to the requirements of this document are also specified.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

EN 764-5:2014, *Pressure equipment — Part 5: Inspection documentation of metallic materials and compliance with the material specification*

EN 10204:2004, *Metallic products — Types of inspection documents*

EN 17263:2019, *Copper and copper alloys — Eddy current testing on the outer surface of rods, bars, hollow rods and wires for the detection of defects by encircling test coil*

EN ISO 2624:1995, *Copper and copper alloys — Estimation of average grain size (ISO 2624:1990)*

EN ISO 6507-1:2018, *Metallic materials — Vickers hardness test — Part 1: Test method (ISO 6507-1:2018)*

EN ISO 6892-1:2019, *Metallic materials — Tensile testing — Part 1: Method of test at room temperature (ISO 6892-1:2019)*

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminology databases for use in standardization at the following addresses:

- IEC Electropedia: available at <https://www.electropedia.org/>
- ISO Online browsing platform: available at <https://www.iso.org/obp>

3.1

wire

wound product of uniform cross-section along its whole length

Note 1 to entry: Rectangles may have round or sharp corners.

3.2

deviation from circular form

difference between the maximum and the minimum diameters measured at any one cross-section of a round product

4 Designation

4.1 Material

4.1.1 General

The material is designated either by symbol or by number (see Tables 1 to 6).

4.1.2 Symbol

The material symbol designation is based on the designation system given in ISO 1190-1:1982.

NOTE Although material symbol designations used in this standard might be the same as those in other standards using the designation system given in ISO 1190-1:1982, the detailed composition requirements are not necessarily the same.

4.1.3 Number

The material number designation is in accordance with the system given in EN 1412:2016.

4.2 Material condition

For the purposes of this document, the following designations, which are in accordance with the system given in EN 1173:2008, apply for the material condition:

M	material condition for the product as manufactured, without specified mechanical properties;
R...	material condition designated by the minimum value of tensile strength requirement for the product with mandatory tensile property requirements;
H...	material condition designated by the minimum value of Vickers hardness requirement for the product with mandatory hardness requirements;
S (suffix)	material condition for a product which is stress relieved.
G...	material condition designated by the mid-range value of grain size requirement for the product with mandatory grain size requirements (Table 13).

NOTE The G... material condition is normally applicable only to round wires in the soft material condition made from alloys given in Tables 3, 4 and non-lead alloys given in Table 2.

Exact conversion between material conditions designated R..., H... and G... is not possible.

Except when the suffix S is used, material condition is designated by only one of the above designations.

4.3 Product

The product designation provides a standardized pattern of designation from which a rapid and unequivocal description of a product can be conveyed in communication. It provides mutual comprehension at the international level with regard to products which meet the requirements of the relevant European Standard.

The product designation is no substitute for the full content of the document.


The product designation for products to this standard shall consist of:

- denomination (Wire);
- number of this European Standard (EN 12166);
- material designation, either symbol or number (see Tables 1 to 6);


- DW for compliance in the chemical composition according to the 4 MS Common Composition List. This information is mandatory in the case in which the product is used for drinking water applications according to the 4 MS Common Composition List and not to be given in other cases (see Bibliography [5]);
- material condition designation (see 4.2 and Tables 7 to 13);
- cross-sectional shape (the following designations shall be used as appropriate: RND for round, SQR for square, RCT for rectangular, HEX for hexagonal, OCT for octagonal, PFL for profile);
- nominal cross-sectional dimension(s) (or the number of the profile or a fully dimensioned and toleranced drawing);
- tolerance class for round, square or polygonal wire, (see Tables 14 and 15);
- for square, rectangular or polygonal wire, the corner shape (the following designations shall be used as appropriate: SH for sharp, RD for rounded), (see Table 17).

The derivation of a product designation is shown in the following examples.

EXAMPLE 1 Wire conforming to this document, in material designated either CuZn40Pb2 or CW617N, for standard applications in material condition H115, rectangular, nominal cross-sectional dimensions 6,0 mm × 5,0 mm, with sharp corners, will be designated as follows:

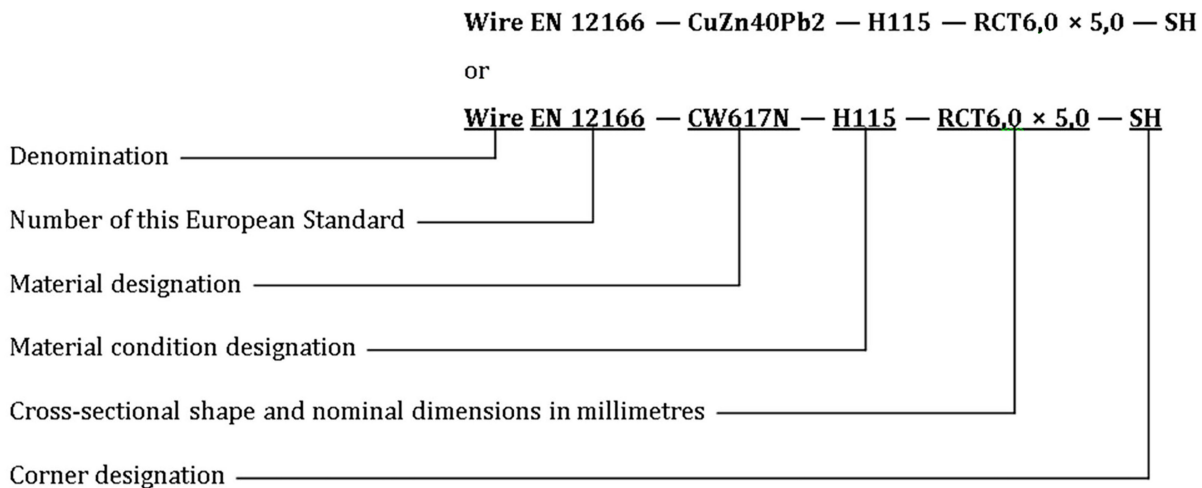

EXAMPLE 2 Wire conforming to this document, in material designated either CuZn40Pb2 or CW617N, for drinking water applications according to the 4 MS Common Composition List, in material condition H115, rectangular, nominal cross-sectional dimensions 6,0 mm × 5,0 mm, with sharp corners, will be designated as follows:

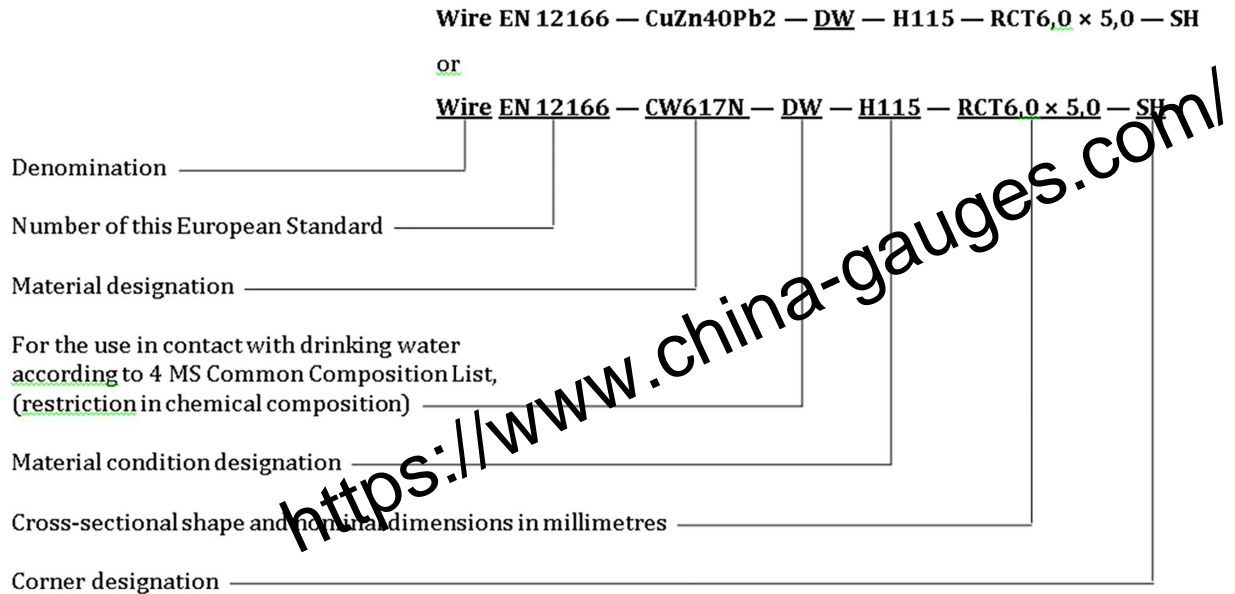

EXAMPLE 3 Wire conforming to this document, in material designated either CuZn39Pb3 or CW614N, for standard applications in material condition R430, round, nominal diameter 6,0 mm, tolerance class B, will be designated as follows:

Wire EN 12166 — CuZn39Pb3 — R430 — RND6,0B

or

Wire EN 12166 — CW614N — R430 — RND6,0B

5 Ordering information

In order to facilitate the enquiry, order and confirmation of order procedures the following information shall be specified:

- a) mass of product required;
- b) denomination (Wire);
- c) number of this European Standard (EN 12166);
- d) material designation (see Tables 1 to 6);
- e) material condition designation (see 4.2 and Tables 7 to 13) if other than M;
- f) DW for compliance in the chemical composition according to the 4 MS Common Composition List. This information is mandatory in the case in which the product is used for drinking water applications according to the 4 MS Common Composition List and not to be given in other cases;
- g) cross-sectional shape;
- h) nominal cross-sectional dimension(s) (diameter or width across-flats);
- i) for round, square and regular polygonal wire, the tolerance class required, unless the tolerance class shall be left to the discretion of the supplier (see Tables 14 and 15); for profiles, the tolerances required (or a drawing with dimensions and tolerances);

- j) for square or rectangular wire, whether 'sharp' or 'rounded' corners are required, unless the corner radii shall be left to the discretion of the supplier (see Table 17);

It is recommended that the product designation, as described in 4.3, is used for items b) to j).

In addition, it shall also state on the enquiry and order any of the following, if required:

- k) for profiles, if the shape is such that the position of the cross-section within the coil, reel, spool or drum is of importance to who make the order, this should be stated on the drawing (See Annex A for illustration);
- l) for profiles, whether mechanical properties are required; if so, the method of test and the level of properties shall be agreed between the involved parties;
- m) whether the products shall be supplied in a thermally stress relieved material condition;
- n) whether special surface quality is required (see 6.6);
- o) whether surface quality test is required (see 6.6) and the class;
- p) whether a certificate of compliance is required (see 9.1);
- q) whether an inspection document is required, and if so, which type (see 9.2);
- r) whether there are any special requirements for marking, labelling or packaging including, if necessary, any limitation on dimensions or mass of coils, spools, reels or drums (see Clause 10).

EXAMPLE 1 Ordering details for 1 000 kg wire for general purposes conforming to EN 12166, in material designated either CuZn39Pb3 or CW614N, in material condition H115, rectangular, nominal cross-sectional dimensions 6,0 mm × 5,0 mm, with sharp corners, in 25 kg coils:

1 000 kg Wire EN 12166 — CuZn39Pb3 — H115 — RCT 6,0 × 5,0 — SH
— 25 kg coils

or

1 000 kg Wire EN 12166 — CW614N — H115 — RCT 6,0 × 5,0 — SH
— 25 kg coils

EXAMPLE 2 Ordering details for 5 000 kg wire for general purposes conforming to EN 12166, in material designated either CuZn40Pb2 or CW617N, for drinking water application according to the 4 MS Common Composition List, in material condition R430, round, nominal diameter 6,0 mm, tolerance class B, on 1 000 kg spools:

5 000 kg Wire EN 12166 — CuZn40Pb2 — DW — R430 — RND6,0B
— 1 000 kg spools

or

5 000 kg Wire EN 12166 — CW617N — DW — R430 — RND6,0B
— 1 000 kg spools

6 Requirements

6.1 Composition

The composition shall conform to the requirements for the appropriate material given in Tables 1 to 6.

Due to developing legislation, specific applications (see 4.3) may require restrictions in the chemical composition. In this case the limitations shall be specified in the ordering information [see Clause 5 list entry f)].

6.2 Mechanical properties

The tensile properties of R... material condition or the hardness properties of H... material condition shall conform to the appropriate requirements given in Tables 7 to 12. The tests shall be carried out in accordance with 8.2 or 8.3.

6.3 Grain size

The grain size of G... material condition shall conform to the appropriate ranges in Table 13. The tests shall be carried out in accordance with 8.4.

6.4 Dimensions and tolerances

6.4.1 Diameter or width across-flats

Diameter or width across-flats at any point shall conform to the tolerances given in Tables 14 to 16.

6.4.2 Shape tolerances

6.4.2.1 Round wire

The deviation from circular form (see 3.2) of round wire less than 3,0 mm diameter, shall not exceed half the range of the tolerance on diameter given in Table 14. The deviation from circular form of round wire equal to or greater than 3,0 mm diameter, shall not exceed the range of the tolerance on diameter given in Table 14.

6.4.2.2 Wire with square or regular cross-section (see above)


The width across-flats, measured at the centre of the faces at any one cross-section, shall not differ by more than half the range of the tolerance given for the size in Table 15.

6.4.3 Corner and edge geometry (wire with square and rectangular cross-section only)

The radii of the corners of wires shall conform to the requirements given in Table 17 for sharp or rounded corners.

For wires with the minimum width across-flats less than 3 mm the corners shall be calculated according to Figure 1. For wires with both widths across-flats equal to or greater than 3 mm, except in cases of dispute, the corners shall be measured directly, either by use of a gauge or an optical projector. In cases of dispute the method by optical projector shall be used.

Wire edges shall be smooth along the product length without discontinuity.

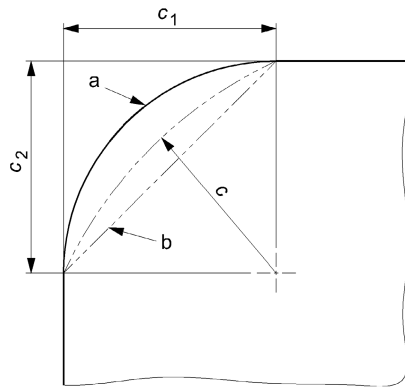

For sizes below 3 mm, the corner radius c is calculated from the formula:

$$c = \frac{c_1 + c_2}{2}$$

and may fall anywhere between fully rounded 'a' and a chamfer 'b'.

Figure 1 — Calculation of corner radii

6.5 Joins

Welds made before the final drawing sequence are permissible. Joins made after the final drawing sequence are not permitted unless there has been agreement between the involved parties on the method of performing and marking these joins.

6.6 Surface quality

The surfaces shall be clean and smooth. The wires may have a superficial film of drawing lubricant or, if annealed or thermally stress relieved, a superficial, dull, iridescent oxide film, securely adherent on the surfaces.

Discontinuous irregularities on the surfaces of the wires are permitted if they are within the dimensional tolerances.

Since surface discontinuities (cracks, overlapping, scale, isolated pores, pits, grooves, etc.) cannot be completely avoided during manufacturing (hot and cold formation, heat treatments, handling and storage) and since they are retained when drawing, agreements shall be made regarding surface quality.

If eddy current test is requested, the test method given in EN 17263:2019 shall be applied using reference standard according to Table 19 for round wire. For polygonal wire the reference standard shall be agreed between the involved parties.

The sensitivity is to be set in such a way that the smallest signal of the borehole(s) just exceeds the response threshold (acceptance level).

Special requirements (e.g. pickling, degreasing, etc.) relating to the surface quality shall be agreed between the involved parties [see Clause 5, list entry n)].

6.7 Internal inclusion

Freedom of internal inclusions cannot be ensured in any copper alloys.

7 Sampling

7.1 General

When required or for use in cases of dispute, an inspection lot shall be sampled in accordance with 7.2 and 7.3.

7.2 Analysis

The sampling rate shall be in accordance with Table 18. A test sample, depending on the analytical technique to be employed, shall be prepared from each sampling unit and used for the determination of the composition.

When preparing the test sample, care should be taken to avoid contaminating or overheating the test sample. Carbide tipped tools are recommended; steel tools, if used, should be made of magnetic material to assist in the subsequent removal of extraneous iron. If the test samples are in finely divided form (e.g. drillings, millings), they should be treated carefully with a strong magnet to remove any particles of iron introduced during preparation.

In cases of dispute concerning the results of analysis, the full procedure given in ISO 1811-2 should be followed.

Results may be used from analyses carried out at an earlier stage of manufacturing the product, e.g. at the casting stage, if the material identity is maintained and if the manufacturer can assure the traceability of the product.

7.3 Tensile, hardness and grain size tests

The sampling rate shall be in accordance with Table 18. Sampling units shall be selected from the finished products. The test samples shall be cut from the sampling units. Test samples, and test pieces prepared from them, shall not be subjected to any further treatment other than any machining operations necessary in the preparation of the test pieces.

8 Test methods

8.1 Analysis

Analysis shall be carried out on the test pieces, or test portions, prepared from the test samples obtained in accordance with 7.2. Except in cases of dispute, the analytical methods used shall be at the discretion of the supplier. In cases of dispute, the methods of analysis to be used shall be agreed between the disputing parties. For expression of results, the rounding rules given in 8.6 shall be used.

8.2 Tensile test

The tensile test shall be performed on a coaxial test piece cut from a test sample obtained in accordance with 7.3. The test shall be carried out in accordance with the method given in EN ISO 6892-1:2019. For expression of results, the rounding rules given in 8.6 shall be used.

For other than round wire, the tensile test results shall be calculated using nominal cross-sectional areas.

Elongation requirements for wire of diameter:

- a) less than 4 mm ($A_{100\text{ mm}}$);
- b) 4 mm up to and including 8 mm ($A_{11,3}$);
- c) greater than 8 mm (A);

are based on original gauge lengths of 100 mm, $11,3 \sqrt{S_0}$ mm and $5,65 \sqrt{S_0}$ mm, respectively, where S_0 is the original cross-sectional area of the test piece in square millimetres.

Elongation values are not applicable to wire sizes less than 0,5 mm (or equivalent cross-sectional areas for polygonal wires).

8.3 Hardness test

Hardness shall be determined on test pieces cut from a test sample obtained in accordance with 7.3. The test shall be carried out in accordance with EN ISO 6507-1:2018 and the indentation made:

- a) for round wire 5 mm diameter and over, at a mid-radius position on a cross-section (see 2nd paragraph below);
- b) for rectangular cross-sections, on the surface of the wire at the approximate mid-point of the major dimension;
- c) for square or polygonal cross-sections, on the surface of the wire at the approximate mid-point of one of the flats;
- d) for profiles, unless otherwise specified at the time of the order, on the cross-section at the mid-point of the thickest part.

In the case of round wire less than 5 mm diameter, the test shall be performed at a position, and by a method, agreed between the involved parties.

For the Vickers test according to EN ISO 6507-1:2018 it is required to use a test force of 49,03 N, 98,07 N or 294,21 N.

8.4 Estimation of average grain size

When at the time of order a grain size requirement is specified [see Clause 5 list entry e)], the estimation of average grain size shall be carried out in accordance with EN ISO 2624:1995.

8.5 Retests

If there is a failure of one, or more than one, of the tests in 8.1, 8.2, 8.3 or 8.4, two test samples from the same inspection lot shall be permitted to be selected for retesting the failed property (properties). One of these test samples shall be taken from the same sampling unit as that from which the original failed test piece was taken, unless that sampling unit is no longer available, or has been withdrawn by the supplier.

If the test pieces from both test samples pass the appropriate test(s), then the inspection lot represented shall be deemed to conform to the particular requirement(s) of this document. If a test piece fails a test, the inspection lot represented shall be deemed not to conform to this document.

8.6 Rounding of results

For the purpose of determining conformity to the limits specified in this document an observed or a calculated value obtained from a test shall be rounded in accordance with the following procedure, which is based upon the guidance given in EN ISO 80000-1. It shall be rounded in one step to the same number of figures used to express the specified limit in this European Standard. Except for tensile strength and 0,2 % proof strength the rounding interval shall be 10 N/mm^2 ¹⁾ and for elongation the value shall be rounded to the nearest 1 %.

The following rules shall be used for rounding:

- a) if the figure immediately after the last figure to be retained is less than 5, the last figure to be retained shall be kept unchanged;
- b) if the figure immediately after the last figure to be retained is equal to or greater than 5, the last figure to be retained shall be increased by one.

9 Certificate of compliance and inspection documentation

9.1 Certificate of compliance

When requested and agreed at the time of the order [see Clause 5 list entry m)] the appropriate certificate of compliance shall be issued for the products.

NOTE The relevant information is available in EN ISO/IEC 17050-1:2010 and EN ISO/IEC 17050-2:2004.

9.2 Inspection documentation

When requested and agreed at the time of the order [(see Clause 5 list entry n)] the appropriate inspection document, in accordance with EN 10204:2004 shall be issued for the products.

For pressure equipment applications, appropriate inspection documentation in accordance with the EN 764-5:2014 shall be requested.

10 Marking, packaging, labelling

Unless otherwise specified at the time of the order, the marking, packaging and labelling shall be left to the discretion of the supplier [see Clause 5 list entry o)].

1) 1 N/mm^2 is equivalent to 1 MPa.

Table 1 — Composition of low alloyed copper alloys

Material designation		Composition (% mass fraction)														Density ^a g/cm ³ approx.			
Symbol	Number	Element	Cu	Be	Co	Ca	Cr	Mn	Ni	P	Pb	Pb	Si	S	Te	Zn	Zr	Others total ^b	
CuBe2	CW101C	min.	Rem.	1,8	—	—	—	—	—	—	—	—	—	—	—	—	—	—	8,3
		max.	—	0,3	—	0,2	—	—	—	—	—	—	—	—	—	—	—	—	0,5
CuBe2Pb	CW102C	min.	Rem.	1,8	—	—	—	—	—	—	0,2	—	—	—	—	—	—	—	8,3
		max.	—	2,0	0,3	—	0,2	—	—	0,3	—	0,6	—	—	—	—	—	—	0,5
CuCo1Ni1Be	CW103C	min.	Rem.	0,4	0,8	—	—	—	0,8	—	—	—	—	—	—	—	—	—	8,3
		max.	—	0,7	1,3	—	0,2	—	1,3	—	—	—	—	—	—	—	—	—	0,5
CuCo2Be	CW104C	min.	Rem.	0,4	2,0	—	—	—	—	—	—	—	—	—	—	—	—	—	8,8
		max.	—	0,7	2,8	—	0,2	—	0,3	—	—	—	—	—	—	—	—	—	0,5
CuCr1Zr	CW106C	min.	Rem.	—	—	0,5	—	—	—	—	—	—	—	—	—	—	0,03	—	8,8
		max.	—	—	—	1,2	0,08	—	—	—	—	—	0,1	—	—	—	0,3	0,2	8,8
CuFe2P	CW107C	min.	Rem.	—	—	—	—	2,1	—	0,015	—	—	—	—	—	0,05	—	—	8,8
		max.	—	—	—	—	2,8	—	—	0,15	0,03	—	—	—	—	0,20	—	0,2	8,8
CuNi1Si	CW109C	min.	Rem.	—	—	—	—	—	1,0	—	—	—	0,4	—	—	—	—	—	8,9
		max.	—	—	—	—	0,2	0,1	1,6	—	0,02	0,7	—	—	—	—	—	0,3	8,9
CuNi2Si	CW111C	min.	Rem.	—	—	—	—	—	1,6	—	—	0,4	—	—	—	—	—	—	8,8
		max.	—	—	—	—	0,2	0,1	2,5	—	0,02	0,8	—	—	—	—	—	0,3	8,8
CuPb1P	CW113C	min.	Rem.	—	—	—	—	—	—	0,003	0,7	—	—	—	—	—	—	—	8,9
		max.	—	—	—	—	—	—	—	0,012	1,5	—	—	—	—	—	—	0,1	8,9
CuSP	CW114C	min.	Rem.	—	—	—	—	—	—	0,003	—	—	—	0,2	—	—	—	—	8,9
		max.	—	—	—	—	—	—	—	0,012	—	—	—	0,7	—	—	—	0,1	8,9

Material designation		Composition % (mass fraction)														Density ^a g/cm ³ approx.	
Symbol	Number	Element	Cu	Be	Co	Cr	Fe	Mn	Ni	P	Pb	Si	S	Te	Zn	Zr	Others total ^b
CuTeP	CW118C	min.	Rem.	—	—	—	—	—	—	0,003	—	—	—	0,4	—	—	—
		max.	—	—	—	—	—	—	—	0,012	—	—	—	0,7	—	—	0,1
CuZr	CW120C	min.	Rem.	—	—	—	—	—	—	—	—	—	—	—	—	0,1	—
		max.	—	—	—	—	—	—	—	—	—	—	—	—	—	0,2	0,1

^a For information only.

^b Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 2 — Composition of copper-nickel-zinc alloys

Material designation		Element	Composition % (mass fraction)								Density ^a g/cm ³ approx.
Symbol	Number		Cu	Fe	Mn	Ni	Pb	Sn	Zn	Others total ^b	
CuNi7Zn39Pb3Mn2	CW400J	min.	47,0	—	1,5	6,0	2,3	—	Rem.	—	8,5
		max.	50,0	0,3	3,0	8,0	3,3	—	—	0,2	
CuNi12Zn24	CW403J	min.	63,0	—	—	11,0	—	—	Rem.	—	8,7
		max.	66,0	0,3	0,5	13,0	0,03	0,03	—	0,2	
CuNi12Zn30Pb1	CW406J	min.	56,0	—	—	11,0	0,5	—	Rem.	—	8,6
		max.	59,0	0,3	0,5	13,0	1,5	0,2	—	0,2	
CuNi18Zn19Pb1	CW408J	min.	59,5	—	—	17,0	0,5	—	Rem.	—	8,7
		max.	62,5	0,3	0,7	19,0	1,5	0,2	—	0,2	
CuNi18Zn20	CW409J	min.	60,0	—	—	17,0	—	—	Rem.	—	8,7
		max.	63,0	0,3	0,5	19,0	0,03	0,03	—	0,2	

^a For information only.
^b Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 3 — Composition of copper-tin alloys

Material designation		Element	Composition % (mass fraction)								Density ^a g/cm ³ approx.
Symbol	Number		Cu	Fe	Ni	P	Pb	Sn	Zn	Others total ^b	
CuSn4	CW450K	min.	Rem.	—	—	0,01	—	3,5	—	—	8,9
		max.	—	0,1	0,2	0,4	0,02	4,5	0,2	0,2	
CuSn5	CW451K	min.	Rem.	—	—	0,01	—	4,5	—	—	8,8
		max.	—	0,1	0,2	0,4	0,02	5,5	0,2	0,2	
CuSn6	CW452K	min.	Rem.	—	—	0,01	—	5,5	—	—	8,8
		max.	—	0,1	0,2	0,4	0,02	7,0	0,2	0,2	
CuSn8	CW453K	min.	Rem.	—	—	0,01	—	7,5	—	—	8,8
		max.	—	0,1	0,2	0,4	0,02	8,5	0,2	0,2	

^a For information only.
^b Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 4 — Composition of copper-zinc alloys

Material designation		Element	Composition ^b % (mass fraction)								Density ^a g/cm ³ approx.	
Symbol	Number		Cu	Al	Fe	Ni	Pb	Sn	Zn	Others total		
CuZn10	CW501L	min.	89,0	—	—	—	—	—	—	Rem.	—	8,8
		max.	91,0	0,02	0,05	0,3	0,05	0,1	—	0,1		
CuZn15	CW502L	min.	84,0	—	—	—	—	—	—	Rem.	—	8,8
		max.	86,0	0,02	0,05	0,3	0,05	0,1	—	0,1		
CuZn20	CW503L	min.	79,0	—	—	—	—	—	—	Rem.	—	8,7
		max.	81,0	0,02	0,05	0,3	0,05	0,1	—	0,1		
CuZn30	CW505L	min.	69,0	—	—	—	—	—	—	Rem.	—	8,5
		max.	71,0	0,02	0,05	0,3	0,05	0,1	—	0,1		
CuZn36	CW507L	min.	63,5	—	—	—	—	—	—	Rem.	—	8,4
		max.	65,5	0,02	0,05	0,3	0,05	0,1	—	0,1		
CuZn37	CW508L	min.	62,0	—	—	—	—	—	—	Rem.	—	8,4
		max.	64,0	0,05	0,1	0,3	0,1	0,1	—	0,1		
CuZn40	CW509L	min.	59,0	—	—	—	—	—	—	Rem.	—	8,4
		max.	61,5	0,05	0,2	0,3	0,2	0,2	—	0,2		
CuZn42	CW510L	min.	57,0	—	—	—	—	—	—	Rem.	—	8,4
		max.	59,0	0,05	0,3	0,3	0,2	0,3	—	0,2		

^a For information only.

^b For drinking water applications, restrictions to the chemical composition of some materials listed in this table may apply according to national regulations/laws, e.g. as specified in the 4 MS Common Composition List.

^c Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 5 — Composition of copper-zinc-lead alloys

Material designation		Element	Composition ^b % (mass fraction)								Density ^a g/cm ³ approx.
Symbol	Number		Cu	Al	Fe	Ni	Pb	Sn	Zn	Others total ^c	
CuZn35Pb1	CW600N	min.	62,5	—	—	—	0,8	—	Rem.	—	8,5
		max.	64,0	0,05	0,1	0,3	1,6	0,1	—	0,1	
CuZn35Pb2	CW601N	min.	62,0	—	—	—	1,6	—	Rem.	—	8,5
		max.	63,5	0,05	0,1	0,3	2,5	0,1	—	0,1	
CuZn36Pb3	CW603N	min.	60,0	—	—	—	2,5	—	Rem.	—	8,5
		max.	62,0	0,05	0,3	0,3	3,5	0,2	—	0,2	
CuZn37Pb2	CW606N	min.	61,0	—	—	—	1,6	—	Rem.	—	8,4
		max.	62,0	0,05	0,2	0,3	2,5	0,2	—	0,2	
CuZn38Pb2	CW608N	min.	60,0	—	—	—	1,6	—	Rem.	—	8,4
		max.	61,0	0,05	0,2	0,3	2,5	0,2	—	0,2	
CuZn39Pb0,5	CW610N	min.	59,0	—	—	—	0,2	—	Rem.	—	8,4
		max.	60,5	0,05	0,2	0,3	0,8	0,2	—	0,2	
CuZn39Pb2	CW612N	min.	59,0	—	—	—	1,6	—	Rem.	—	8,4
		max.	60,0	0,05	0,3	0,3	2,5	0,3	—	0,2	
CuZn39Pb3	CW614N	min.	57,0	—	—	—	2,2	—	Rem.	—	8,4
		max.	59,0	0,05	0,3	0,3	3,5	0,3	—	0,2	
CuZn40Pb2	CW617N	min.	57,0	—	—	—	1,6	—	Rem.	—	8,4
		max.	59,0	0,05	0,3	0,3	2,2	0,3	—	0,2	
CuZn40Pb1	CW627N	min.	57,0	—	—	—	0,8	—	Rem.	—	8,4
		max.	59,0	0,05	0,3	0,3	1,6	0,3	—	0,2	

^a For information only.

^b For drinking water applications, restrictions to the chemical composition of some materials listed in this table may apply according to national regulations/laws, e.g. as specified in the 4 MS Common Composition List.

^c Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 6 — Composition of complex copper-zinc alloys

Material designation		Composition ^b % (mass fraction)												Density ^a g/cm ³
Symbol	Number	Element	Cu	Al	Fe	Mn	Ni	P	Pb	Si	Sn	Zn	others ^c total	approx.
CuZn36Sn1Pb	CW712R	min.	61,0	—	—	—	—	—	0,2	—	1,6	Rem.	—	8,3
		max.	63,0	—	0,1	—	0,2	—	0,6	—	1,5	—	0,2	
CuZn40Mn1Pb1	CW720R	min.	57,0	—	—	0,5	—	—	1,0	—	—	Rem.	—	8,3
		max.	59,0	0,2	—	1,5	0,6	—	2,0	0,1	0,3	—	0,3	
CuZn21Si3P	CW724R	min.	75,0	—	—	—	—	0,02	—	2,7	—	Rem.	—	8,3
		max.	77,0	0,05	0,3	0,05	0,2	0,10	0,10	3,5	0,3	—	0,2	
CuZn36Si1P	CW726R	min.	60,5	—	—	—	—	0,01	—	0,7	—	Rem.	—	8,3
		max.	64,5	—	0,2	0,2	0,2	0,10	0,10	1,3	0,2	—	0,3	

^a For information only.

^b For drinking water applications, restrictions to the chemical composition of some materials listed in this table may apply according to national regulations/laws, e.g. as specified in the 4 MS Common Composition List.

^c Elements not reported and elements reported in the table for which no upper and lower limits are defined, are included in other totals.

Table 7 — Mechanical properties of wire of low alloyed copper alloys

Designations		Material condition	Diameter ^a		Tensile strength R_m N/mm ² (MPa) min.	0,2 % proof strength $R_{p0,2}$ N/mm ² (MPa) min.	Elongation ^b			Hardness	
Material	Number		from	up to and including			$A_{100\text{ mm}}$ %	$A_{11,3}$ %	A	min.	max.
		M	All		As manufactured						
CuBe2 CuBe2P	CW101C CW102C	R1150	0,2	10	1 150	1 000	—	—	2	—	—
		H350	1,5	10	—	—	—	—	—	350	420
		R1300	0,2	10	1 300	1 100	—	—	2	—	—
		H370	1,5	10	—	—	—	—	—	370	440
		M	All		As manufactured						
CuCo1Ni1Be CuCo2Be	CW103C CW104C	R680	1	10	680	550	3	6	10	—	—
		H230	1,5	10	—	—	—	—	—	230	290
		R730	1	10	730	610	2	5	8	—	—
		H240	1,5	10	—	—	—	—	—	240	330

Designations		Material condition	Diameter ^a		Tensile strength ^a R_m N/mm ² (MPa)	Yield strength ^a $R_{p0,2}$ N/mm ² (MPa)	Elongation ^b			Hardness	
							$A_{100\text{ mm}}$ %	$A_{11,3}$ %	A	min.	max.
CuCr1Zr	Number	M	All		As manufactured						
		R370	2	10	370	250	8	12	16	—	—
		H125	2	10	—	—	—	—	—	125	170
		R430	2	10	430	350	5	8	10	—	—
		H145	2	10	—	—	—	—	—	145	185
		R470	2	10	470	420	3	6	8	—	—
		H160	2	10	—	—	—	—	—	160	190
CuFe2P	Number	M	All		As manufactured						
		R300	1,5	12	300	110	17	20	23	—	—
		H050	1,5	12	—	—	—	—	—	50	100
		R400	0,3	8	400	350	6	7	—	—	—
		H110	1,5	8	—	—	—	—	—	110	140
		R500	0,1	3	500	450	2	—	3	—	—
		H150	1,5	3	—	—	—	—	—	150	180

Designations		Material condition	Diameter ^a		Tensile strength ^a R _m N/mm ² (MPa)	Yield strength ^a R _{p0,2} N/mm ² (MPa)	Elongation ^b			Hardness		
							A _{100 mm} %	A _{11,3} %	A	min.	max.	
CuNi1Si	Number	M	All		As manufactured							
		R440	1,5	15	440	300	6	8	16	—	—	
		H130	1,5	15	—	—	—	—	—	130	190	
		R540	1,5	15	540	470	4	6	12	—	—	
		H150	1,5	15	—	—	—	—	—	150	200	
		R590	1,5	12	590	540	3	5	10	—	—	
		H170	1,5	12	—	—	—	—	—	170	220	
CuNi2Si	Number	M	All		As manufactured							
		R550	1,5	15	550	430	5	8	15	—	—	
		H160	1,5	15	—	—	—	—	—	160	210	
		R600	1,5	15	600	520	4	6	10	—	—	
		H175	1,5	15	—	—	—	—	—	175	220	
		R640	1,5	12	640	590	3	5	8	—	—	
		H190	1,5	12	—	—	—	—	—	190	250	

<https://www.mmm.com>

Designations		Material condition	Diameter ^a		Tensile strength ^b R_m N/mm ² (MPa)	Yield strength ^b $R_{p0,2}$ N/mm ² (MPa)	Elongation ^b			Hardness		
							$A_{100\text{ mm}}$ %	$A_{11,3}$ %	A	min.	max.	
Symbol	Number		mm	mm	min.	min.	min.	min.	min.	min.	min.	max.
		M	All	All			As manufactured					
		R250	1,5	12	250	180	2	4	7	—	—	—
		H090	1,5	12	—	—	—	—	—	90	130	—
		R300	1,5	12	300	240	2	3	5	—	—	—
		H110	1,5	12	—	—	—	—	—	110	140	—
		R360	1,5	10	360	300	—	—	—	—	—	—
		H120	1,5	10	—	—	—	—	—	120	—	—
		M	All	All			As manufactured					
		R250	0,1	12	250	170	8	15	20	—	—	—
		H080	1,5	12	—	—	—	—	—	80	120	—
		R280	0,1	12	280	210	6	12	15	—	—	—
		H095	1,5	12	—	—	—	—	—	95	135	—
		R350	0,1	10	350	260	5	10	12	—	—	—
		H125	1,5	10	—	—	—	—	—	125	165	—
		M	All	All			As manufactured					
		R250	0,1	12	250	170	8	15	20	—	—	—
		H080	1,5	12	—	—	—	—	—	80	120	—
		R280	0,1	12	280	210	6	12	15	—	—	—
		H095	1,5	12	—	—	—	—	—	95	135	—
		R350	0,1	10	350	260	5	10	12	—	—	—
		H125	1,5	10	—	—	—	—	—	125	165	—

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Table 8 — Mechanical properties of wire of copper-nickel-zinc alloys

Designations		Material Symbol	Material code	Diameter ^a mm		Tensile strength		Proof strength		Elongation ^b		Hardness			
Material	Number			from	up to and including	R_m N/mm ² (MPa)	$R_{p0,2}$ N/mm ² (MPa)	A_{100} mm %	$A_{11,3}$ %	A	min.	max.	min.	max.	
CuNi7Zn39Pb3Mn2 CW400J				M	All	As manufactured									
				H115	1,5	12	—	—	—	—	—	—	115	—	
				R500	1,5	12	500	350	8	10	12	—	—	—	
				H130	1,5	12	—	—	—	—	—	—	130	170	
				R600	1,5	12	600	400	2	3	5	—	—	—	
				H165	1,5	12	—	—	—	—	—	—	165	200	
				R700	1,5	5	700	500	—	—	—	—	—	—	
				H190	1,5	5	—	—	—	—	—	—	190	—	—

Designations		Material condition	Diameter ^a mm from up to and including		Tensile strength R_m N/mm ² (MPa) min.	Yield strength		Elongation ^b			Hardness		
						$R_{p0,2}$ N/mm ² (MPa) min.	max.	A_{100} mm %	$A_{11,3}$ %	A %	min.	max.	
CuNi12Zn24	CW403J	M	All		As manufactured								
		R380	1,5	20	380	—	290	28	33	38	—	—	
		H090	1,5	20	—	—	—	—	—	—	90	130	
		R450	1,5	12	450	200	—	8	10	12	—	—	
		H130	1,5	12	—	—	—	—	—	—	130	160	
		R540	0,1	10	540	400	—	2	3	5	—	—	
		H170	1,5	10	—	—	—	—	—	—	170	200	
		R640	0,1	4	640	500	—	—	—	—	—	—	
		H200	1,5	4	—	—	—	—	—	—	200	—	
		R800	0,1	1,5	800	700	—	—	—	—	—	—	
H220	—	1,5	—	—	—	—	—	—	—	220	—		

http://www.en12166.com

Designations		Material condition	Diameter ^a mm from up to and including		Tensile strength R_m N/mm ² (MPa) min.	Yield strength		Elongation ^b		Hardness	
						$R_{p0.2}$ N/mm ² (MPa) min.	max.	A_{100} mm %	$A_{11.3}$ %	min.	max.
		M	All			As manufactured					
		R420	1,5 12	420	260	12	16	20	—	—	—
		H115	1,5 12	—	—	—	—	—	115	155	—
		R520	1,5 10	520	420	3	5	6	—	—	—
		H135	1,5 10	—	—	—	—	—	135	165	—
		R650	1,5 8	650	580	—	—	—	—	—	—
		H160	1,5 8	—	—	—	—	—	160	190	—
Material	Symbol	Number									
CuNi12Zn30Pb1 CuNi18Zn19Pb1		CW406J CW408J									

<http://www.en12166.com>

Designations		Material condition	Diameter ^a mm from up to and including	Tensile strength R_m N/mm ² (MPa) min.	Proof strength		Elongation ^b			Hardness	
Material	Number				$R_{p0,2}$ N/mm ² (MPa) min.	$R_{p0,2}$ N/mm ² (MPa) max.	A_{100} mm %	$A_{11,3}$ %	A %	min.	max.
As manufactured											
M			All								
	R400		1,5 20	400	—	290	25	30	35	—	—
	H105		1,5 20	—	—	—	—	—	—	105	145
	R480		0,1 12	480	250	—	7	9	11	—	—
	H145		1,5 12	—	—	—	—	—	—	145	185
CuNi18Zn20	R580		0,1 10	580	400	—	2	3	5	—	—
	H180		1,5 10	—	—	—	—	—	—	180	220
	R660		0,1 4	660	550	—	—	—	—	—	—
	H210		1,5 4	—	—	—	—	—	—	210	—
	R800		0,1 1,5	800	750	—	—	—	—	—	—
	H230		— 1,5	—	—	—	—	—	—	230	—

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Table 9 — Mechanical properties of wire of copper-tin alloys

Designations		Material condition	Diameter ^a		Tensile strength R_m N/mm ² (MPa) min.	0,2 % proof strength $R_{p0,2}$ N/mm ² (MPa) min.		Elongation ^b		Hardness		
Material	Number		from	up to and including		A_{100} mm %	$A_{11,3}$ %	min.	max.	min.	max.	
CuSn4	CW450K	M	All		As manufactured							
		R330	1,5	20	330	—	220	35	40	45	—	
		H085	1,5	20	—	—	—	—	—	—	85	115
		R420	0,1	12	420	220	—	20	25	30	—	—
		H125	1,5	12	—	—	—	—	—	—	125	155
		R520	0,1	8	520	380	—	5	6	—	—	—
		H150	1,5	8	—	—	—	—	—	—	150	185
		R650	0,1	4	650	500	—	—	—	—	—	—
		H210	1,5	4	—	—	—	—	—	—	210	—
		R850	0,1	1,5	850	750	—	—	—	—	—	—
H230	—	1,5	—	—	—	—	—	—	230	—		

Designations		Material condition	Diameter ^a mm from up to and including		Tensile strength ^c R_{m} N/mm ² (MPa) min.	Yield strength ^d $R_{p0,2}$ N/mm ² (MPa) min. max.		Elongation ^b		Hardness		
						$R_{p0,2}$ N/mm ² (MPa) min.	$R_{p0,2}$ N/mm ² (MPa) max.	A_{100} mm %	$A_{11,3}$ %	min.	max.	
CuSn5	Number	M	All		As manufactured		As manufactured					
		R340	1,5	20	340	—	270	35	40	45	—	—
		H085	1,5	20	—	—	—	—	—	—	85	115
		R420	0,1	12	420	220	—	20	25	30	—	—
		H125	1,5	12	—	—	—	—	—	—	125	165
		R520	0,1	8	520	400	—	3	5	—	—	—
		H155	1,5	8	—	—	—	—	—	—	155	190
		R700	0,1	4	700	600	—	—	—	—	—	—
		H190	1,5	4	—	—	—	—	—	—	190	225
		R900	0,1	1,5	900	800	—	—	—	—	—	—
H245	—	—	—	—	—	—	—	—	—	245	—	
CuSn6	Number	M	All		As manufactured		As manufactured					
		R340	1,5	20	340	—	270	35	40	45	—	—
		H085	1,5	20	—	—	—	—	—	—	85	115
		R420	0,1	12	420	220	—	20	25	30	—	—
		H125	1,5	12	—	—	—	—	—	—	125	165
		R520	0,1	8	520	400	—	3	5	—	—	—
		H155	1,5	8	—	—	—	—	—	—	155	190
		R700	0,1	4	700	600	—	—	—	—	—	—
		H190	1,5	4	—	—	—	—	—	—	190	225
		R900	0,1	1,5	900	800	—	—	—	—	—	—
H245	—	—	—	—	—	—	—	—	—	245	—	

Designations		Material condition	Diameter ^a mm from up to and including		Tensile strength ^b R_{m} N/mm ² (MPa) min.	Proof of strength		Elongation ^b			Hardness	
						$R_{p0,2}$ N/mm ² (MPa) min.	max.	A_{100} mm %	$A_{11,3}$ %	A	min.	max.
CuSn8	CW453K	M	All	As manufactured								
		R390	0,1	12	390	—	280	35	40	45	—	—
		H090	1,5	12	—	—	—	—	—	—	90	130
		R450	0,1	12	450	280	—	18	22	26	—	—
		H140	1,5	12	—	—	—	—	—	—	140	170
		R550	0,1	12	550	400	—	10	12	15	—	—
		H170	1,5	12	—	—	—	—	—	—	170	200
		R620	0,1	8	620	500	—	4	6	—	—	—
		H185	1,5	8	—	—	—	—	—	—	185	—
		R750	0,1	4	750	680	—	—	—	—	—	—
		H220	1,5	4	—	—	—	—	—	—	220	—
		R920	0,1	1,5	920	800	—	—	—	—	—	—
		H265	—	1,5	—	—	—	—	—	—	265	—

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Table 10 — Mechanical properties of wire of copper-zinc alloys

Designations		Material condition	Diameter ^a		Tensile strength		0,2 % proof strength		Elongation ^b		Hardness		
Material	Number		from	up to and including	R_m N/mm ² (MPa)	min.	$R_{p0,2}$ N/mm ² (MPa)	min.	A_{100} mm %	$A_{11,3}$ %	A	min.	max.
CuZn10	CW501L	M	All		As manufactured								
		R240	4	20	240	—	—	150	43	45	47	—	—
		H050	4	20	—	—	—	—	—	—	—	50	100
		R320	1,5	20	320	220	—	20	23	25	—	—	—
		H095	1,5	20	—	—	—	—	—	—	—	95	125
		R380	0,5	10	380	280	—	10	11	12	—	—	—
		H115	1,5	10	—	—	—	—	—	—	—	115	155
		R440	0,5	6	440	330	—	4	5	—	—	—	—
		H135	1,5	6	—	—	—	—	—	—	—	135	180
		R530	0,5	4	530	450	—	—	—	—	—	—	—
H160	1,5	4	—	—	—	—	—	—	—	160	—		

Designations		Material condition	Diameter ^a		Tensile strength ^c R_m N/mm ² (MPa) min.	Yield strength ^c $R_{p0,2}$ N/mm ² (MPa) min. max.	Elongation ^b		Hardness			
Material	Number		mm	up to and including			A_{100} mm %	$A_{11,3}$ %	A	min.	max.	
CuZn15	CW502L	M	All		As manufactured							
		R260	4	20	260	—	170	33	35	38	—	—
		H060	4	20	—	—	—	—	—	—	60	120
		R340	1,5	20	340	200	—	18	20	22	—	—
		H105	1,5	20	—	—	—	—	—	—	105	135
		R430	0,5	5	430	350	—	6	8	—	—	—
		H135	1,5	5	—	—	—	—	—	—	135	175
		R530	0,5	3	530	450	—	3	—	—	—	—
H155	1,5	3	—	—	—	—	—	—	155	—		
CuZn20	CW503L	M	All		As manufactured							
		R260	4	20	260	—	170	40	42	45	—	—
		H065	4	20	—	—	—	—	—	—	65	105
		R360	1,5	20	360	210	—	16	18	20	—	—
		H105	1,5	20	—	—	—	—	—	—	105	140
		R450	0,5	5	450	300	—	5	6	—	—	—
		H140	1,5	5	—	—	—	—	—	—	140	200
		R540	0,1	3	540	450	—	2	—	—	—	—
H165	1,5	3	—	—	—	—	—	—	165	—		

Designations		Diameter ^a	Tensile strength ^b R_m N/mm ² (MPa) min.	Yield strength ^b $R_{p0,2}$ N/mm ² (MPa) min.	Elongation ^b		Hardness				
					A_{100} mm %	$A_{11,3}$ %		A %	min.	max.	
Material	Material condition	mm	up to and including		As manufactured						
Symbol	Number	mm	mm		mm						
CuZn30	M	All									
	R280	4	20	280	—	250	37	40	43	—	—
	H070	4	20	—	—	—	—	—	—	70	120
	R370	1,5	20	370	230	—	12	14	16	—	—
	H110	1,5	20	—	—	—	—	—	—	110	140
	R460	0,5	5	460	310	—	4	7	—	—	—
	H140	1,5	5	—	—	—	—	—	—	140	—
	R550	0,1	3	550	450	—	3	—	—	—	—
	H165	1,5	3	—	—	—	—	—	—	165	—

Designations		Diameter ^a mm	Tensile strength ^c R_m N/mm ² (MPa)	Yield strength ^c $R_{p0,2}$ N/mm ² (MPa)	Elongation ^b			Hardness	
					Material condition	A_{100} mm %	$A_{11,3}$ %	A %	min.
Symbol	Number		min.	min.	max.	min.	min.	min.	max.
		All	As manufactured						
	M								
	R290	0,5	290	—	230	30	40	45	—
	H055	1,5	—	—	—	—	—	—	55 110
	R370	0,5	370	240	—	10	12	14	—
	H095	1,5	—	—	—	—	—	—	95 140
CuZn36 CuZn37	CW507L CW508L	0,5	460	330	—	4	6	—	—
	H115	1,5	—	—	—	—	—	—	115 155
	R550	0,5	550	450	—	2	5	—	—
	H130	1,5	—	—	—	—	—	—	130 170
	R700	0,5	700	550	—	—	—	—	—
	H160	1,5	—	—	—	—	—	—	160

<https://www.china-dresses.com>

Designations		Material condition	Diameter ^a		Tensile strength ^b R_m N/mm ² (MPa) min.	Yield strength $R_{p0,2}$ N/mm ² (MPa) min. max.	Elongation ^b		Hardness			
Material	Number		mm	up to and including			A_{100} mm %	$A_{11,3}$ %	A	min.	max.	
CuZn40	CW509L	M	All		As manufactured							
		R360	0,5	20	360	—	300	10	15	20	—	—
		H080	1,5	20	—	—	—	—	—	—	80	110
		R410	0,5	14	410	220	—	8	10	12	—	—
		H100	1,5	14	—	—	—	—	—	—	100	160
		R500	0,5	8	500	350	—	2	5	—	—	—
H130	1,5	8	—	—	—	—	—	—	130	—		
CuZn42	CW510L	M	All		As manufactured							
		R360	6	20	360	—	320	—	15	20	—	—
		H095	6	20	—	—	—	—	—	—	95	130
		R430	0,5	14	430	220	—	6	8	10	—	—
		H115	1,5	14	—	—	—	—	—	—	115	170
		R500	0,5	8	500	350	—	2	5	—	—	—
H145	1,5	8	—	—	—	—	—	—	145	—		

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Designations		Diameter ^a mm up to and including	Tensile strength ^b $R_{p0,2}$ N/mm ² (MPa)		Elongation ^b		Hardness		
Material	Number		min.	max.	A_{100} mm %	$A_{11,3}$ %	min.	max.	
		M	As manufactured						
		R360	360	—	—	15	20	—	—
		H095	—	—	—	—	—	95	130
		R430	430	220	6	8	10	—	—
		H115	—	—	—	—	—	115	170
		R500	500	350	2	5	—	—	—
		H145	—	—	—	—	—	145	—
CuZn39Pb3									
CuZn40Pb2	CW614N								
CuZn40Pb1	CW617N								
	CW627N								

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Table 12 — Mechanical properties of wire of complex copper-zinc alloys

Designations		Material condition	Diameter ^a		Tensile strength		0,2% proof strength		Elongation ^b			Hardness			
Symbol	Number		from	up to and including	R_m N/mm ² (MPa)	min.	max.	$R_{p0,2}$ N/mm ² (MPa)	min.	max.	$A_{100\text{ mm}}$ %	$A_{11,3}$ %	A	min.	max.
CuZn36Sn1Pb	CW712R	M	All												
				0,5	20	340	160	—	15	20	25	—	—	—	—
				1,5	20	—	—	—	—	—	—	—	—	85	125
				0,1	8	400	200	—	10	16	—	—	—	—	—
				1,5	8	—	—	—	—	—	—	—	—	110	140
CuZn40Mn1Pb1	CW720R	M	All												
				0,5	20	390	180	—	10	16	20	—	—	—	—
				1,5	20	—	—	—	—	—	—	—	—	100	135
				0,1	8	440	250	—	8	15	—	—	—	—	—
				1,5	8	—	—	—	—	—	—	—	—	110	155

Designations		Material condition	Diameter ^a		Tensile strength ^b R_m N/mm ² (MPa)	proof strength $R_{p0,2}$ N/mm ² (MPa)	Elongation ^b		Hardness		
							$A_{100\text{ mm}}$ %	$A_{11,3}$ %	min.	max.	min.
CuZn21Si3P	Number	M	All				As manufactured				
		R500	0,5	20	500	—	12	13	15	—	
		H110	1,5	20	—	—	—	—	—	110	170
		R600	0,5	8	600	300	10	11	—	—	—
		H130	1,5	8	—	—	—	—	—	130	190
		R670	0,5	8	670	400	8	9	—	—	—
		H160	1,5	8	—	—	—	—	—	160	220
		R750	0,5	8	750	450	2	3	—	—	—
H200	1,5	8	—	—	—	—	—	200	—		
CuZn36Si1P	Number	M	All				As manufactured				
		R460	0,5	20	460	—	6	8	10	—	—
		H100	1,5	20	—	—	—	—	—	100	180
		R500	0,5	8	500	270	2	5	—	—	—
		H130	1,5	8	—	—	—	—	—	130	210
		R560	0,5	8	560	410	2	5	—	—	—
		H150	1,5	8	—	—	—	—	—	150	220
		R630	0,5	8	630	450	2	3	—	—	—
H160	1,5	8	—	—	—	—	—	160	—		

^a Or equivalent cross-sectional area for polygonal wire.

^b For Elongation requirements refer to 8.2.

Table 13 — Grain size designations

Grain size designation	Range of average grain size mm	
	min.	max.
G015	—	—
G025	0,015	0,035
G040	0,025	0,055
G055	0,035	0,070
G085	0,050	0,120
G100	0,070	—

NOTE 1 Average grain size ranges other than those in this table are subject to agreement between the involved parties.
NOTE 2 The G... material condition is normally applicable only to round wires in the soft material condition made from alloys given in Tables 1, 3, 4 and to non-lead alloys in Table 2.

Table 14 — Tolerances on diameter of round wire

Dimensions in millimetres

Nominal diameter		Tolerance ^a				
over	up to and including	class A	class B	class C	class D	class E
—	0,25	±0,005	—	—	0 - 0,025	0 - 0,006
0,25	0,5	±0,008	—	—	0 - 0,03	0 - 0,010
0,5	1,0	±0,012	—	—	0 - 0,03	0 - 0,014
1,0	2,0	±0,02	0 - 0,10	0 - 0,06	0 - 0,04	0 - 0,025
2,0	4,0	±0,03	0 - 0,10	0 - 0,06	0 - 0,04	0 - 0,025
4,0	6,0	±0,04	0 - 0,12	0 - 0,08	0 - 0,05	0 - 0,030
6,0	10,0	±0,06	0 - 0,15	0 - 0,09	0 - 0,06	0 - 0,036
10,0	20,0	±0,08	0 - 0,18	0 - 0,11	0 - 0,07	0 - 0,043

^a For deviation from circular form refer to 6.4.2.1.

Table 15 — Tolerances on width across-flats of square or regular polygonal wire

Dimensions in millimetres

Nominal width across-flats		Tolerance ^a		
over	up to and including	class A	class B	class C
—	0,50	±0,015	—	—
0,5	1,0	±0,02	—	—
1,0	2,0	±0,03	—	—
2,0	4,0	±0,05	0 - 0,12	0 - 0,08
4,0	6,0	±0,06	0 - 0,12	0 - 0,08
6,0	10,0	±0,08	0 - 0,15	0 - 0,09
10,0	20,0	±0,10	0 - 0,18	0 - 0,11

^a For deviation from square or regular cross-section form refer to 6.4.2.2.

Table 16 — Tolerances on width and thickness of rectangular wire

Dimensions in millimetres

Nominal width across-flats		Tolerance on width	Tolerance on thickness for range of thickness						
over	up to and including		up to and including 1,0	over 1,0 up to and including 2,0	over 2,0 up to and including 4,0	over 4,0 up to and including 6,0	over 6,0 up to and including 10,0	over 10,0 up to and including 18,0	over 18,0
—	1,0	±0,02	±0,02	—	—	—	—	—	—
1,0	2,0	±0,03	±0,02	±0,03	—	—	—	—	—
2,0	4,0	±0,05	±0,02	±0,03	±0,05	—	—	—	—
4,0	6,0	±0,06	±0,02	±0,03	±0,05	±0,06	—	—	—
6,0	10,0	±0,08	±0,02	±0,03	±0,05	±0,07	±0,08	—	—
10,0	18,0	±0,10	—	±0,03	±0,05	±0,07	±0,09	±0,10	—
18,0	—	±0,15	—	—	±0,05	±0,07	±0,09	±0,10	±0,15

Table 17 — Corner radii for square or rectangular wire

Dimensions in millimetres

Nominal thickness		Radii for sharp and rounded corners	
over	up to and including	sharp max.	rounded min. & max.
—	0,60	0,05	0,05 to 0,25
0,60	1,5	0,08	0,08 to 0,25
1,5	3,0	0,2	0,2 to 0,3
3,0	6,0	0,3	0,3 to 0,5
6,0	10,0	0,4	0,4 to 0,8
10,0	—	0,5	0,5 to 1,2

Table 18 — Sampling rate

Nominal diameter ^a mm		Mass of inspection lot for one test sample kg
over	up to and including	up to and including
0,1	0,8	200
0,8	3,0	500
3,0	10,0	1 000
10,0	—	2 000

If piece weights are greater than the weight of inspection lot indicated, the sampling rate may be reduced to one per piece weight.

NOTE Larger quantities require sampling in proportion, up to a maximum of three test samples.

^a Or equivalent cross-sectional area for polygonal wire.

Table 19 — Acceptance parameters for reference standard

Dimensions in millimetres

Wire size		Hole diameter	Hole depth (min.)
over and including	up to		
5	10	1,0 ± 0,05	0,8
10	20 ^a	1,5 ± 0,05	0,8


^a Including 20.

Annex A
(informative)

Position of wire cross-section within a coil, reel, spool or drum

The position of the wire cross-section within the coil/reel/spool/drum is illustrated in Figure A.1 for coil and Figure A.2 for reel/spool/drum.


If a cross-section is characterized by one clearly defined base line the position of this base line in relation to the axis of the coil/reel/spool/drum may be specified by letter A, B, C or D, see Figure A.3 for coil and Figure A.4 for reel/spool/drum.

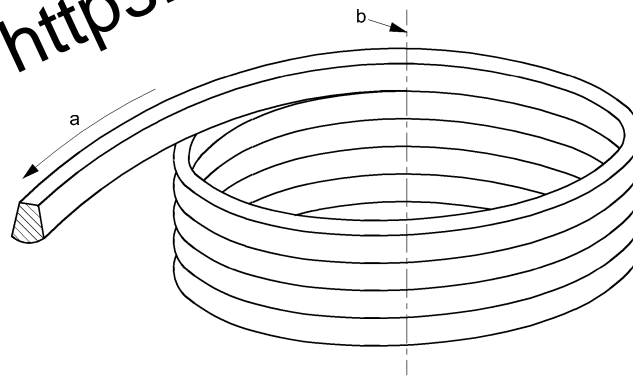

Key

- a direction of decoiling
- b axis


Figure A.1 — Illustration of position of wire cross-section within the coil (bunched wound or stagger/traverse wound)

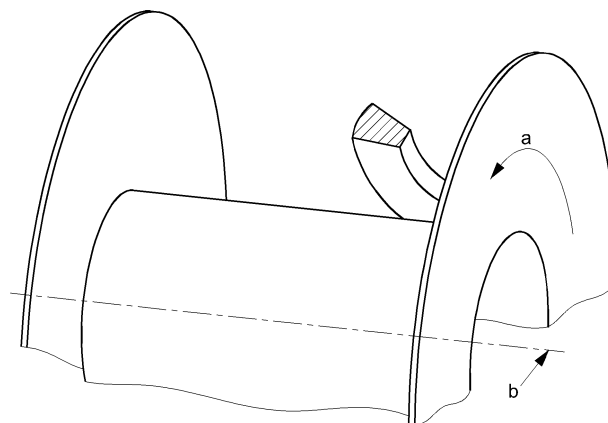

Key


- a direction of decoiling
- b axis

Figure A.2 — Illustration of position of wire cross-section within the reel/spool/drum (stagger/traverse wound)

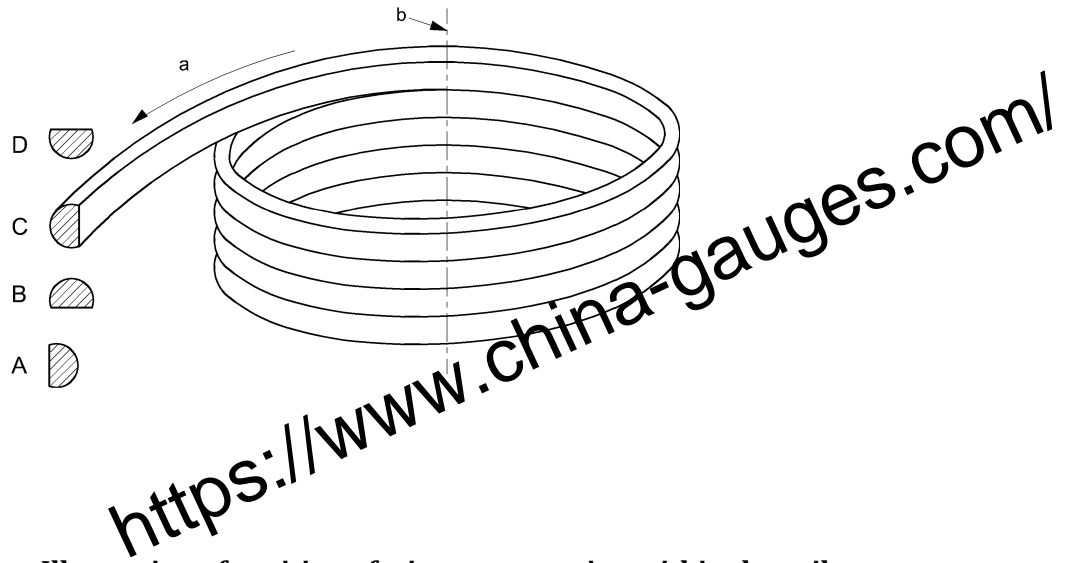

Key
a direction of decoiling
b axis

Figure A.3 — Illustration of position of wire cross-section within the coil (bunched wound or stagger/traverse wound)

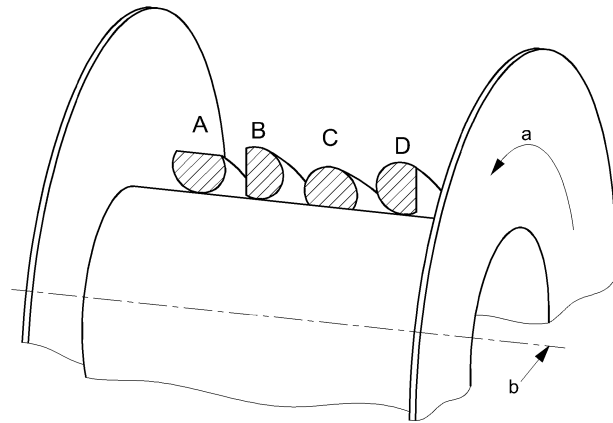

Key
a direction of decoiling
b axis

Figure A.4 — Illustration of position of wire cross-section within the reel/spool/drum (stagger/traverse wound)

Annex ZA
(informative)

Relationship between this European Standard and the essential requirements of Directive 2014/68/EU (Pressure equipment Directive) aimed to be covered

This European Standard has been prepared under a Commission's standardization request M/601 to provide one voluntary means of conforming to essential requirements of Directive 2014/68/EU.

Once this standard is cited in the Official Journal of the European Union under that Directive, compliance with the normative clauses of this standard given in Table ZA.1 confers, within the limits of the scope of this standard, a presumption of conformity with the corresponding essential requirements of that Directive and associated EFTA regulations.

For this harmonized supporting standard for materials, presumption of conformity to the Essential Requirements of the Directive is limited to technical data of the material in the standard and does not presume adequacy of the material to specific equipment. Consequently, the technical data stated in the material standard should be assessed against the design requirements of the specific equipment to verify that the Essential Requirements of the Pressure Equipment Directive (PED) are satisfied.

Table ZA.1 — Correspondence between this European Standard and Annex I of Directive 2014/68/EU (Pressure equipment Directive)

Essential Requirements of Directive 2014/68/EU	Clause(s)/subclause(s) of this EN	Remarks/Notes
4.1 (a)	6.2	Mechanical properties
4.3	9.2, 2 nd paragraph	Conformity of material and manufacturer's certified documentation

WARNING 1 — Presumption of conformity stays valid only as long as a reference to this European Standard is maintained in the list published in the Official Journal of the European Union. Users of this standard should consult frequently the latest list published in the Official Journal of the European Union.

WARNING 2 — Other Union legislation may be applicable to the product(s) falling within the scope of this standard.

Bibliography

- [1] EN 1173:2008, *Copper and copper alloys — Material condition designation*
- [2] EN 1412:2016, *Copper and copper alloys — European numbering system*
- [3] EN 12163, *Copper and copper alloys — Rod for general purposes*
- [4] EN ISO 9001, *Quality management systems — Requirements (ISO 9001)*
- [5] EN ISO 80000-1, *Quantities and units — Part 1: General (ISO 80000-1)*
- [6] EN ISO/IEC 17050-1:2010, *Conformity assessment — Supplier's declaration of conformity — Part 1: General requirements (ISO/IEC 17050-1:2004)*
- [7] EN ISO/IEC 17050-2:2004, *Conformity assessment — Supplier's declaration of conformity — Part 2: Supporting documentation (ISO/IEC 17050-2:2004)*
- [8] ISO 1190-1:1982, *Copper and copper alloys — Code of designation — Part 1: Designation of materials*
- [9] ISO 1811-2, *Copper and copper alloys — Selection and preparation of samples for chemical analysis — Part 2: Sampling of wrought products and castings*
- [10] "Acceptance for metallic materials used for products in contact with drinking water", 4 MS Common approach, Part B "4 MS Common Composition List"
(<https://www.umweltbundesamt.de/themen/wasser/trinkwasser/trinkwasser-verteilen/erkennung-harmonisierung-4ms-initiative>)

<https://www.china-gauges.com/>

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than one device provided that it is accessible by the sole named user only and that only one copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than one copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright and Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email cservices@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email: cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK